

Oxide Ion Conductivity in the Hexagonal Perovskite Derivative Ba₃MoNbO_{8.5}

S. Fop¹, J. M. S. Skakle¹, A. C. Mclaughlin¹, P. A. Connor², J. T. S. Irvine², R. I. Smith³ and E.

J. Wildman¹

¹The Chemistry Department, University of Aberdeen, Meston Walk, Aberdeen, AB24 3UE,

UK.

²School of Chemistry, University of St Andrews, St Andrews, Fife KY16 9ST, UK.

³ISIS Facility, Rutherford Appleton Laboratory, Harwell, Didcot OX11 0DE, UK.

Abstract

Oxide ion conductors are important materials with a range of technological applications and are currently used as electrolytes for solid oxide fuel cells (SOFCs) and solid oxide electrolyser cells (SOECs). Here we report the crystal structure and electrical properties of the hexagonal perovskite derivative Ba₃MoNbO_{8.5}. Ba₃MoNbO_{8.5} crystallises in a hybrid of the 9R hexagonal perovskite and palmierite structures. This is a new and so far unique crystal structure that contains a disordered distribution of (Mo/Nb)O₆ octahedra and (Mo/Nb)O₄ tetrahedra. Ba₃MoNbO_{8.5} shows a wide stability range and exhibits predominantly oxide ion conduction over a pO₂ range of 10⁻²⁰ – 1 atm with a bulk conductivity of 2.2 x 10⁻³ S cm⁻¹ at 600 °C. The high level of conductivity in a new structure family suggests that further study of hexagonal perovskite derivatives containing mixed tetrahedral and octahedral geometry could open up new horizons in the design of oxygen conducting electrolytes.

Oxide ion conductors have received much attention in recent years due to their application as electrolytes for solid oxide fuel cells (SOFCs) and solid oxide electrolyser cells (SOECs), oxygen sensors and oxygen separation membranes^{1, 2, 3, 4, 5, 6, 7, 8, 9}. So far several series of fast oxide ion conductors have been reported including fluorite-like systems^{3, 6}, silicon and germanium apatites¹⁰, $\text{La}_2\text{Mo}_2\text{O}_9$ (LAMOX) materials⁷, $\text{Bi}_4\text{V}_2\text{O}_{11}$ derivatives¹¹ and complex oxides with GaO_4 tetrahedral moieties^{9, 12}. SOFCs are highly efficient devices that convert chemical energy into electrical energy and require an electrolyte material with specific properties. A good SOFC electrolyte must exhibit negligible electron conductivity, high oxide ion transport and stability in both oxidising and reducing atmospheres as it is in contact with both the anode and cathode side of the fuel cell. For ease of manufacture and variable temperature applications it is desirable to lower the SOFCs' operating temperature to an intermediate range (400 – 600 °C). The oxide ion conductivity of a material is strongly dependent on the crystal structure and hence in order to reach this objective, it is important to discover and characterise new structural families of oxide ion conducting materials.

The perovskite family appears to offer great potential for the discovery of new oxide ion conductors due to its capability of adopting numerous structural derivatives. Several perovskite materials with sizeable oxide ion conductivity have been reported including strontium and magnesium-doped lanthanum gallates (LSGM)¹³ and more recently the well-known ferroelectric material $\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$ ⁸. Hexagonal perovskites form when BO_6 octahedra share faces and different stacking sequences of the cubic (corner-sharing BO_6 octahedra) and hexagonal (face-sharing BO_6 octahedra) AO_3 layers can give rise to a variety of unique crystal structures. There have been accounts of hexagonal systems exhibiting mixed oxide ion and electronic conductivity but these materials tend to exhibit low conductivities and low transport numbers^{14, 15, 16}.

Here we report the crystal structure and electrical properties of the hexagonal perovskite derivative $\text{Ba}_3\text{MoNbO}_{8.5}$. A bulk conductivity of $2.2 \times 10^{-3} \text{ S cm}^{-1}$ is observed at $600 \text{ }^\circ\text{C}$ which is comparable to other prominent oxide ion conductors¹⁻¹². $\text{Ba}_3\text{MoNbO}_{8.5}$ crystallises in a hybrid of the 9R hexagonal and palmierite structures^{17, 18}. The crystal structure contains both Mo/NbO_6 octahedra and Mo/NbO_4 tetrahedra with intrinsic oxygen vacancies.

Results

Sample Characterisation

$\text{Ba}_3\text{MoNbO}_{8.5}$ has an oxygen stoichiometry between that of the 9R polytype¹⁷ and the palmierite structure¹⁸. An electron diffraction and high resolution electron microscopy study previously showed that the oxygen defects with respect to the 9R polytype $(\text{hhc})_3$ leads to an ordered distribution of octahedra and tetrahedra in a 3:2 ratio in the cubic layers¹⁹. The X-ray diffraction pattern of $\text{Ba}_3\text{MoNbO}_{8.5}$ could be indexed with the space group $R\bar{3}m$ H ($a = 5.921 (1) \text{ \AA}$; $c = 21.0908 (2) \text{ \AA}$) in agreement with previous results¹⁹ and there was no evidence of impurities. X-ray diffraction data were also recorded after $\text{Ba}_3\text{MoNbO}_{8.5}$ was annealed at $600 \text{ }^\circ\text{C}$ for 24 hours in flowing O_2 , N_2 and 5 % H_2/N_2 . The X-ray diffraction data show that post annealing there is no change in crystal structure with no evidence of impurities and that $\text{Ba}_3\text{MoNbO}_{8.5}$ is stable at temperatures between $20 \text{ }^\circ\text{C}$ and $650 \text{ }^\circ\text{C}$ and at temperatures $> 1100 \text{ }^\circ\text{C}$. $\text{Ba}_3\text{MoNbO}_{8.5}$ was also annealed in 5 % H_2/N_2 at a higher temperature of $1200 \text{ }^\circ\text{C}$ for 24 hours with no evidence of impurity phases in the X-ray diffraction pattern, indicating that $\text{Ba}_3\text{MoNbO}_{8.5}$ is surprisingly stable in 5 % H_2/N_2 (Supplementary Figure 1). The results demonstrate that the $\text{Ba}_3\text{MoNbO}_{8.5}$ phase presents wider phase stability range under reducing conditions than other leading oxide ion conductors such as LAMOX²⁰ and the Bi and Ce oxides⁵.

Conductivity of Ba₃MoNbO_{8.5}

The electrical properties of a 95 % dense pellet of Ba₃MoNbO_{8.5} were measured by a.c. impedance spectroscopy between 300 – 600 °C. A typical impedance spectrum of Ba₃MoNbO_{8.5} recorded in dry air at 315 °C is presented in Figure 1 (a). An electrode response is observed in the low frequency region at all temperatures which is indicative of ionic conduction in a material with partially blocking electrodes²¹. The bulk and grain boundary responses are evidenced at higher frequencies with respective capacitance values of C_B ~ 6.0 pF cm⁻¹ and C_{Gb}, ~ 0.15 nF cm⁻¹. The complex impedance plots, Z*, show that the bulk arc is visible at temperatures up to 450 °C. As the temperature increases, the grain boundary arc along with a low slope electrode element indicative of Warburg type diffusion is observed. At the highest temperatures the electrode response is the main component, and turns over as might be expected for finite length Warburg diffusion (Figure 1 (b)). Such evolution is indicative of oxide ion mobility²¹. Furthermore the electrode response was found to become less resistive when the oxygen content of the atmosphere increased, strongly indicating oxide ion mobility. Equivalent circuit analysis was utilised to extract the individual bulk, grain boundary and electrode responses at each temperature (see Supplementary Information).

The Arrhenius plot of the grain boundary and bulk conductivity of Ba₃MoNbO_{8.5} is presented in Figure 1 (b). The grain boundaries constitute the most resistive part, thus dominating the total resistivity of the material. The grain boundary conductivity is $5.9 \times 10^{-4} \text{ S cm}^{-1}$ at 600 °C with an activation energy of $1.223 \pm 0.015 \text{ eV}$. The bulk conductivity is $2.2 \times 10^{-3} \text{ S cm}^{-1}$ at 600 °C with an activation energy of $1.211 \pm 0.016 \text{ eV}$. A change in slope is evidenced at temperatures > 500 °C, with the activation energy lowering to $0.71 \pm 0.018 \text{ eV}$. At 600 °C the bulk conductivity is comparable to other leading solid oxide electrolyte materials such as Na_{0.5}Bi_{0.5}TiO₃⁸, Zr_{0.92}Y_{0.08}O_{1.96}²², LAMOX⁷ and La_{0.9}Sr_{0.1}Ga_{0.9}Mg_{0.1}O_{2.9}¹³ and much greater than

perovskite derivatives such as $\text{Ba}_2\text{In}_2\text{O}_5$ ²³ and NdBaInO_4 ²⁴. NdBaInO_4 has an ionic conductivity of $\sim 1 \times 10^{-6} \text{ S cm}^{-1}$ at 600 °C (Figure 2) although it has recently been shown that it is possible to further enhance the ionic conductivity of NdBaInO_4 by substitution of Sr^{2+} for Nd^{3+} ; $\text{Nd}_{0.9}\text{Sr}_{0.1}\text{BaInO}_4$ has an ionic conductivity of $\sim 1 \times 10^{-4} \text{ S cm}^{-1}$ at 600 °C²⁵.

Electromotive force (EMF) measurements using an oxygen concentration cell at selected temperatures between 450 °C and 600 °C showed oxygen transport numbers of 0.97 – 0.99 in air/ O_2 and 0.90 – 0.94 in air/5% H_2 in Ar, suggesting that $\text{Ba}_3\text{MoNbO}_{8.5}$ is an oxide ion conductor with negligible electrical conductivity in air/ O_2 and that a small amount of electronic conduction is observed in air/5% H_2 in Ar (Figure 1(c)). The temperature dependence of the conductivity recorded in a wet air flow resulted in a reduction in both the bulk and total conductivity compared to the same measurement in a dry air flow. This suggests that there is no proton conduction in this material (Figure 4 in the Supporting Information). Degradation of the electrical conductivity with time has been seen in other promising oxide ion conductors, for example in the $\text{Bi}_4\text{V}_2\text{O}_{11}$ derivatives²⁶. Conductivity data versus time were recorded at 600 °C and there was no evidence of degradation of the conductivity during the 12 days that the impedance spectra were recorded. (Figure 5 in the Supporting Information).

Figure 1(d) shows the $p\text{O}_2$ dependence of the total conductivity of $\text{Ba}_3\text{MoNbO}_{8.5}$ at 600 °C. At oxygen partial pressures $< 10^{-20}$ atm, an electronic n-type contribution to the total conductivity is evidenced. At oxygen partial pressures $< 10^{-20}$ atm, reduction of the Mo^{6+} and/or Nb^{5+} cations results in the formation of oxygen vacancies and electronic defects. The latter exhibit greater mobility than the oxygen vacancies so that the conductivity is dominated by the concentration of the electronic defects, which is proportional to $p\text{O}_2^{-1/4}$. The conductivity appears to be independent of oxygen partial pressure over the range $10^{-20} - 10^{-$

⁴ atm. There is evidence of a plateau between $pO_2 = 10^{-20} - 10^{-4}$ atm, indicating oxide ionic conductivity with negligible electronic conduction over this range of pO_2 .

Between $pO_2 = 10^{-3} - 1$ atm the variation of the total conductivity with oxygen partial pressure is unusual. Upon increasing pO_2 from $10^{-3} - 0.21$ atm the total conductivity decreases. As pO_2 increases further from $0.21 - 1$ atm the total conductivity rises so that there is a minimum in σ_{tot} at $pO_2 = 0.21$. The transport number recorded in air/ O_2 at $600^\circ C$ is 0.99. Thermogravimetric analysis data recorded at $600^\circ C$ in both flowing N_2 and O_2 showed no significant oxygen gain or loss, suggesting that the presence of the conductivity minimum cannot be related to any significant change of the overall phase composition. One possibility is that at $pO_2 > 0.21$ atm the increase in σ_{tot} is a result of a structural change such as a redistribution or ordering of the oxygen vacancies. Variable temperature neutron diffraction experiments in flowing oxygen, nitrogen and air will be required to corroborate this. An alternative scenario is that these changes are related to changes in composition at the grain boundary at high temperatures and high pO_2 .

Neutron Diffraction

In order to further investigate the crystal structure of $Ba_3MoNbO_{8.5}$, neutron diffraction data were recorded at ambient temperature on the GEM diffractometer at ISIS. Rietveld refinement²⁷ of the neutron data was performed using the GSAS package with the EXPGUI interface^{28, 29}. The background was fitted by the Chebyshev polynomial function and the peak shapes were modelled using a pseudo-Voigt function. $Ba_3MoNbO_{8.5}$ has previously been described to have intrinsic oxygen vacancies and intertwined regions of Mo/ NbO_6 octahedra and Mo/ NbO_4 tetrahedra¹⁹. A poor fit to the neutron data was obtained upon using the model previously reported for $Ba_3MoNbO_{8.5}$ ¹⁹ in a high resolution electron microscopy study. There

was no evidence of an ordered distribution of octahedra and tetrahedra within the cubic layers. A poor fit was also obtained to the model previously reported for the stoichiometrically similar compound $\text{Ba}_3\text{VWO}_{8.5}$ ³⁰ which contains a purely octahedral coordination of vanadium and tungsten.

Previous electron diffraction¹⁹ and Raman³¹ studies had clearly indicated the presence of both $(\text{Mo/Nb})\text{O}_6$ octahedra and $(\text{Mo/Nb})\text{O}_4$ tetrahedra within the crystal structure. A hybrid model of the palmierite and 9R structures was therefore constructed (Figure 3(a), Table 1) and an excellent Rietveld fit to this model is obtained ($\chi^2 = 2.4$, $R_p = 3.29\%$ and $R_{wp} = 3.24\%$ (Figure 4)). The oxygen content in $\text{Ba}_3\text{MoNbO}_{8.5}$ is intermediate between the two structural types. Both the 9R and the palmierite structures have an $(\text{hhc})_3$ stacking sequence but oxygen vacancies in the cubic layers of the palmierite $(\text{hhc})_3$ sequence results in the formation of tetrahedral B cations (Fig. 3). The oxygen atom at Wyckoff position $18h$ is common to both the 9R and palmierite structures. The palmierite structure also has an oxygen atom at Wyckoff position $6c$ whereas the 9R structure has an oxygen atom at position $9e$. The hybrid model contains oxygen on all three sites and metals on both the $6c$ and $3b$ Wyckoff positions (Table 1). Refining the oxygen site occupancies results in an overall oxygen stoichiometry of 8.5; the oxygen (O(1)) at position $18h$ is fully occupied and partial occupancy of O(2) and O(3) is observed (Table 1). Mo^{6+} and Nb^{5+} have very similar X-ray and neutron scattering lengths and so it was not possible to determine the ratio of Mo:Nb on each site. It was assumed that the Mo^{6+} and Nb^{5+} cations were disordered over the $6c$ and $3b$ sites. The Ba fractional occupancies refined to within $\pm 1\%$ of the full occupancy and were fixed at 1.0.

The atomic displacement parameters, U , were modelled anisotropically for all atoms. The atomic displacement parameters for Ba ions were constrained to be the same, as were the atomic displacement parameters for Mo/Nb on the $6c$ and $3b$ sites. Disorder of the oxygen

atom, O(3), within the Mo/NbO₄ tetrahedra was evidenced by large U_{11} , U_{22} and U_{12} values. This was modelled by using a single isotropic U factor for O(3) and splitting the site as shown in Table 1, Figure 3. The Ba(2) and Mo(1)/Nb(1) cations and the ideal O(3) 6c position are all located on the 3-fold axis and the Ba(2)-Mo(1)/Nb(1) distance is ~ 4.07 Å. It is proposed that the disorder of oxygen onto the 36i positions arises as a result of the short distance between Ba(2) and Mo(1)/Nb(1) so that the disorder stabilises the structure resulting in longer and more realistic Ba(2)-O(3) and Mo(1)/Nb(1)-O(3) bond lengths. Similar structural disorder has been reported for the mixed conducting hexagonal perovskite Ba₇Y₂Mn₃Ti₂O₂₀¹⁴. The thermal ellipsoids of O(1) and O(2) and Ba/Nb atoms are displayed in Figure 3(b). The Mo/Nb sites also exhibit highly anisotropic thermal motion ($U_{11} = U_{22} = 0.0049(2)$ Å²; $U_{33} = 0.0498(9)$ Å²; $U_{12} = 0.0025(1)$ Å²). The bond lengths and angles obtained from Rietveld refinement of the neutron diffraction data (Fig. 3(b); Supplementary Table 1) demonstrate that the (Mo/Nb)O₆ and (Mo/Nb)O₄ polyhedra are distorted in Ba₃MoNbO_{8.5}. Similar bond lengths and angles have been reported for other materials containing mixed tetrahedral/octahedral coordination of Mo and Nb atoms³².

Discussion

Ba₃MoNbO_{8.5} is the first hexagonal perovskite derivative to exhibit significant oxide ion conductivity. Ba₃MoNbO_{8.5} crystallises with an unusual and unique hybrid structure containing a disordered distribution of (Mo/Nb)O₆ octahedra and (Mo/Nb)O₄ tetrahedra. The crystal structure of Ba₃MoNbO_{8.5} contains intrinsic oxygen vacancies. Given the partial occupancies of the 9e and 36i sites the conductivity is most likely a result of migration of the O(2) ion from the (Mo/Nb)O₆ octahedra to vacant sites on neighbouring (Mo/Nb)O₄ tetrahedra site. A single crystal X-ray diffraction study has shown that the high oxide ion

mobility observed in $\text{La}_2\text{Mo}_2\text{O}_9$ ³³ is facilitated by the ability of Mo^{6+} to adopt variable coordination environments. The same ability has been reported for Nb^{5+} in the high temperature structure of the mixed ionic and electronic conductor $\text{Ba}_4\text{Nb}_2\text{O}_9$ ³⁴. It is highly likely that the variable co-ordination environment for Mo^{6+} and/or Nb^{5+} in $\text{Ba}_3\text{MoNbO}_{8.5}$ is important for producing a low energy migration pathway for the oxide ions.

The $(\text{Mo}/\text{Nb})\text{O}_6$ and $(\text{Mo}/\text{Nb})\text{O}_4$ polyhedra are also clearly distorted in $\text{Ba}_3\text{MoNbO}_{8.5}$ (Fig. 3(b); Supplementary Table 1). It has previously been reported that both d^0 cations Mo^{6+} and Nb^{5+} are susceptible to out of centre displacement of the metal-oxygen octahedra as a result of a 2nd order Jahn-Teller distortion³⁵. The magnitude of the out of centre distortion increases with increasing formal charge and decreases with increasing size of the cation so that a sizeable distortion is expected for Mo^{6+} . It is therefore likely that the observed distortions of the $(\text{Mo}/\text{Nb})\text{O}_6$ and $(\text{Mo}/\text{Nb})\text{O}_4$ polyhedra, combined with the anisotropic thermal displacement of the Mo/Nb cations and the variable coordination geometry of the Mo^{6+} and/or Nb^{5+} cation enables facile mobility of the oxide ions through the anion vacancies in the $\text{Ba}_3\text{MoNbO}_{8.5}$ structure. Further computer modelling is required to establish the diffusion pathways of the oxide ions in $\text{Ba}_3\text{MoNbO}_{8.5}$.

The bulk ionic conductivity of $\text{Ba}_3\text{MoNbO}_{8.5}$ at 600 °C is comparable to other leading oxide conductors and considerably larger than those reported for other perovskite derivatives such as NdBaInO_4 (Fig. 2) which exhibits predominantly oxide ion conductivity over the $p\text{O}_2$ range 3.0×10^{-19} to 3.2×10^{-11} atm²⁴. EMF and conductivity versus oxygen partial pressure measurements, give evidence that oxide ionic conductivity is observed for $\text{Ba}_3\text{MoNbO}_{8.5}$ over the $p\text{O}_2$ range 10^{-20} – 1 atm at 600 °C. The electronic n-type contribution to the total conductivity observed for $p\text{O}_2 < 10^{-20}$ is most likely due to the reduction of Mo^{6+} at low $p\text{O}_2$; substitution of Mo^{6+} with the more stable W^{6+} cation could further increase the ionic

conduction window, as reported for W-doped LAMOX materials²⁰. Ba₃MoNbO_{8.5} exhibits good ionic transport number values of 0.99 in air/O₂ and 0.92 in air/5% H₂ in Ar at 600 °C, which corroborate the results obtained from *p*O₂ measurements. Ba₃MoNbO_{8.5} is stable under both flowing 5% H₂/N₂ and O₂ and presents a wider stability range under reducing conditions than other leading oxide ion conductors such as the Bi and Ce oxides⁵. There is also no degradation of the electrical conductivity with time and no evidence of proton conduction. Appropriate chemical doping should result in a further increase of the bulk conductivity so that Ba₃MoNbO_{8.5} could be an excellent candidate as an electrolyte for intermediate temperature fuel cells upon further chemical modification. Hexagonal perovskite derivatives containing mixed tetrahedral and octahedral geometry warrant further investigation.

Methods

Material synthesis. Ba₃MoNbO_{8.5} samples were prepared by solid-state reaction of stoichiometric amounts of BaCO₃ (99.999%, Aldrich), MoO₃ (99.5+%, Aldrich) and Nb₂O₅ (99.99%, Aldrich). The starting materials were ground, pressed into a pellet and calcined in an alumina crucible at 900 °C for 10 hours. The pellet was subsequently reground, pelleted and heated at 1100 °C for 48 hours and then cooled to room temperature at 5 °C/min. The latter heating step was repeated until a phase pure product was obtained.

X-ray and neutron powder diffraction. Room temperature X-ray powder diffraction patterns were collected on a PANalytical X'Pert Powder diffractometer equipped with a Cu K α tube. Data were recorded in the range 20° < 2 θ < 70°, with a step size of 0.013°. Time of flight (TOF) neutron powder diffraction experiments were performed on the General Material Diffractometer (GEM) at ISIS (Rutherford Appleton Laboratory, Harwell Oxford, United

Kingdom) at ambient temperature on 5 grams of $\text{Ba}_3\text{MoNbO}_{8.5}$ sealed in an 8 mm vanadium can. Data were acquired in the TOF range 500 – 18000 μs using the four bank detectors with a total scan time of 2 hours.

Thermogravimetric analysis. The oxygen content of $\text{Ba}_3\text{MoNbO}_{8.5}$ was determined by thermogravimetric analysis in N_2 and O_2 atmospheres using a Stanton Redcroft 780 thermal analyser. $\text{Ba}_3\text{MoNbO}_{8.5}$ was heated under an oxygen flow of 50 mL/min from room temperature to 600 °C at 5 °C per minute and then held at 600 °C for 14 hours. This was then repeated with a nitrogen flow of 50 mL/min.

Electrical characterisation. For the impedance spectroscopy measurements, a pellet of ~ 10 mm diameter and ~ 1.5 mm thickness was prepared from a powder sample of $\text{Ba}_3\text{MoNbO}_{8.5}$ and sintered at 1100 °C for 48 hours (to achieve > 95 % of the theoretical density). Pt electrodes were painted on both sides of the pellet using a Pt-paste (Metalor 6082). Impedance spectra were recorded with a Solartron 1260 impedance analyser in the frequency range 0.1 Hz – 1 MHz with an applied alternating voltage of 0.1 V. Data were recorded upon cooling from 600 °C to 300 °C in a sealed tube furnace under the flow of dry and moist air, measuring every 15 °C and allowing 2 hours of equilibration at each temperature step. The obtained data were corrected by the geometrical factor of the sample and treated with the ZView software (Scribner Associates, Inc.).

Concentration cell measurements were performed on a pellet of $\text{Ba}_3\text{MoNbO}_{8.5}$ with 97 % of the theoretical density. The sample was coated on both faces with Pt-paste and cemented on to the holder to assure gas tightness. Open circuit voltages were recorded on cooling from 600 °C to 450 °C every 50 °C, leaving enough time for the sample to reach equilibrium with the surrounding atmosphere, using a Solartron 1287 electrochemical interface. In all of the

measurements one side of the pellet was exposed to a flow of dry air and the other to dry flows of oxygen or a mixture of 5 % hydrogen in argon.

The conductivity dependence on the oxygen partial pressure (pO_2) of a porous pellet of $Ba_3MoNbO_{8.5}$ with ~ 70 % of the theoretical density was recorded at 600 °C over a pO_2 range of $1 - 10^{-27}$ atm (monitored with a YSZ sensor). The pO_2 range was controlled over the $1 - 10^{-4}$ atm range by dilution of O_2 with Ar and for less than 10^{-20} atm by 5% H_2 in an argon flow.

The conductivity was continuously measured using a Keithley 182 Sensitive Digital Voltmeter with a four electrode configuration.

References

¹ Goodenough, J. B. Oxide-ion electrolytes. *Annu. Rev. Mater. Res.* **33**, 91–128 (2003).

² Steele, B. & Heinzel, A. Materials for fuel-cell technologies. *Nature* **414**, 345–352 (2001).

³ Malavasi, L., Fisher, C. a J. & Islam, M. S. Oxide-ion and proton conducting electrolyte materials for clean energy applications: structural and mechanistic features. *Chem. Soc. Rev.* **39**, 4370–4387 (2010).

⁴ Brett, D. J. L., Atkinson, A., Brandon, N. P. & Skinner, S. J. Intermediate temperature solid oxide fuel cells. *Chem. Soc. Rev.* **37**, 1568–1578 (2008).

⁵ Wachsman, E. D. & Lee, K. T. Lowering the temperature of solid oxide fuel cells. *Science* **334**, 935–939 (2011).

⁶ Kuang, X., Payne, J. L., Johnson, M. R. & Radosavljevic, I. E. Remarkably high oxide ion conductivity at low temperature in an ordered fluorite-type superstructure. *Angew. Chemie - Int. Ed.* **51**, 690–694 (2012).

-
- ⁷ Lacorre, P., Goutenoire, F., Bohnke, O., Retoux, R. & Laligant, Y. Designing fast oxide-ion conductors based on $\text{La}_2\text{Mo}_2\text{O}_9$. *Nature* **404**, 856–858 (2000).
- ⁸ Li, M., Pietrowski, M. J., De Souza, R. A., Zhang, H., Reaney, I. M., Cook, S. N., Kilner, J. A. & Sinclair, D. C. A family of oxide ion conductors based on the ferroelectric perovskite $\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$. *Nat. Mater.* **13**, 31–35 (2014).
- ⁹ Kuang, X., Green, M. A., Niu, H., Zajdel, P., Dickinson, C., Claridge, J. B., Jantsky, L. & Rosseinsky, M. J. Interstitial oxide ion conductivity in the layered tetrahedral network melilite structure. *Nat. Mater.* **7**, 498–504 (2008).
- ¹⁰ Kendrick, E., Islam, M. S. & Slater, P. R. Developing apatites for solid oxide fuel cells: insight into structural, transport and doping properties. *J. Mater. Chem.* **10**, 3104–3111 (2007).
- ¹¹ Abraham, F., Debreuille-Gresse, M. F., Mairesse, G. & Nowogrocki, G. Phase transition and ionic conductivity in $\text{Bi}_4\text{V}_2\text{O}_{11}$ an oxide with layered structure. *Solid State Ionics* **30**, 529–532 (1988).
- ¹² Kendrick, E., Kendrick, J., Knight, K. S., Islam, M. S. & Slater, P. R. Cooperative mechanisms of fast-ion conduction in gallium-based oxides with tetrahedral moieties. *Nat. Mater.* **6**, 871–875 (2007).
- ¹³ Ishihara, T., Matsuda, H. & Y. Takita. Doped LaGaO_3 perovskite type oxide as a new oxide ionic conductor. *J. Am. Chem. Soc.* **116**, 3801–3803 (1994).
- ¹⁴ Kuang, X., Allix, M., Ibberson, R. M., Claridge, J. B., Niu, H. & Rosseinsky, M. J. Oxygen vacancy ordering phenomena in the mixed-conducting hexagonal perovskite $\text{Ba}_7\text{Y}_2\text{Mn}_3\text{Ti}_2\text{O}_{20}$. *Chem. Mater.* **19**, 2884–2893 (2007).

-
- ¹⁵ Ling, C. D., Avdeev, M., Kutteh, R., Kharton, V. V., Yaremchenko, A. A., Fialkova, S., Sharma, N., Macquart, R. B., Hoelzel, M. & Gutmann, M. Structures, phase transitions, hydration, and ionic conductivity of Ba₄Nb₂O₉. *Chem. Mater.* **21**, 3853–3864 (2009).
- ¹⁶ Ling, C. D., Avdeev, M., Kutteh, R., Kharton, V. V., Yaremchenko, A. A., Macquart, R. B. & Hoelzel, M. Structures, phase transitions, hydration and ionic conductivity of Ba₄Ta₂O₉. *Chem. Mater.* **22**, 532–540 (2009).
- ¹⁷ Durif, A. Structure cristalline des orthovanadates et orthoarseniates de baryum et de strontium. *Acta Cryst.* **12**, 420-421 (1959).
- ¹⁸ Susse, P. & Buerger, M. J. The structure of Ba₃(VO₄)₂. *Z. Krist.* **131**, 161-174 (1970).
- ¹⁹ García-González, E., Parras, M. & González -Calbet, J. M. Electron microscopy study of a new cation deficient perovskite-like oxide: Ba₃MoNbO_{8.5}. *Chem. Mater.* **10**, 1576–1581 (1998).
- ²⁰ Marrero-Lopez, D., Canales-Vazquez, J., Ruiz-Morales, J.C., Irvine, J.T.S. & Nunez, P. Electrical conductivity and redox stability of La₂Mo_{2-x}W_xO₉ materials. *Electrochimica Acta*, **50**, 4385–4395 (2005).
- ²¹ Irvine, J. T. S., Sinclair, D. C. & West, A. R. Electroceramics: characterisation by impedance spectroscopy. *Adv. Mater.* **2**, 132-138 (1990).
- ²² Kwon, Oh H. & Choi, G. M. Electrical conductivity of thick film YSZ. *Solid State Ionics*, **177**, 3057-3062 (2007).
- ²³ Goodenough, J. B., Ruiz-Diaz, J. E. & Zhen, Y. S. Oxide-ion conduction in Ba₂In₂O₅ and Ba₃In₂MO₈ (M = Ce , Hf , or Zr). *Solid State Ionics* **44**, 21–31 (1990).
- ²⁴ Fujii, K. et al. New perovskite-related structure family of oxide-ion conducting materials NdBaInO₄. *Chem. Mater.* **26**, 2488–2491 (2014).

-
- ²⁵ Fujii, K. et al. Improved oxide ion conductivity of NdBaInO₄ by Sr doping. *J. Mater. Chem. A* **3**, 11985–11990 (2015).
- ²⁶ Krok, F., Malys, M., Dygas, J.R., Bogusz, W. & Abrahams, I. Time Dependent Effects in Electrical Conductivity in BiZnVOX. *Mol. Phys. Rep.* **27**, 46-52 (2000).
- ²⁷ Rietveld, H. M. Line profiles of neutron powder-diffraction peaks for structure refinement. *Acta Crystallogr.*, **22**, 151-152 (1967).
- ²⁸ Larson, A. C.; Von Dreele, R. B. General Structure Analysis System (GSAS), Los Alamos National Laboratory, Technical Report No. LAUR86-748 (2004) (unpublished).
- ²⁹ Toby, B. H. *EXPGUI*, a graphical user interface for *GSAS*, *J. Appl. Cryst.* **34**, 210-213 (2001).
- ³⁰ Moessner, B. & Kemmler-Sack, S. 9R Stapelvarianten vom typ Ba₃(B,B')₂O_{9-y} mit B,B' = Mo, W,V, Ti *J. Less-Com. Met*, **114**, 333-341 (1985).
- ³¹ Brown Holden, A. A. , Reedyk, M., García-González, E., Parras, M. & Gonzalez-Calbet, J. M. Raman scattering study of cation-deficient Ba_n(MoNb)_{n-δ}O_{3n-x} and related perovskite-like oxides. *Chem. Mater.* **12**, 2287-2291 (2000).
- ³² García-González, E., Parras, M. & González -Calbet, J. M. Crystal structure of an unusual polytype: 7H-Ba₇Nb₄MoO₂₀. *Chem. Mater.* **11**, 433-437 (1999).
- ³³ Evans, I. R., Howard, J. A. K. & Evans, J. S. O. The crystal structure of α-La₂Mo₂O₉ and the structural origin of the oxide ion migration pathway, *Chem. Mater.* **17**, 4074-4077 (2005).
- ³⁴ Dunstan, M. T., Blanc, F., Avdeev, M., McIntyre, G. J., Grey, C. P. & Ling, C. D. Long-range-ordered coexistence of 4-, 5-, and 6-coordinate niobium in the mixed ionic-electronic conductor γ-Ba₄Nb₂O₉, *Chem. Mater.*, **25**, 3154-3161 (2013).
- ³⁵ Kunz, M. & Brown, D. I. Out-of-center distortions around octahedrally coordinated d⁰ transition metals, *J. Solid State Chem.* **115**, 395-406 (1995).

Acknowledgements

This research was supported by the Northern Research Partnership and the University of Aberdeen. We also acknowledge STFC-GB for provision of beamtime at ISIS.

Author Contributions

E.W. and S.F. performed the synthesis and electrical and structural characterisation of $\text{Ba}_3\text{MoNbO}_{8.5}$ and analysed the data. P.C. performed the pO_2 measurements and transport measurements at the University of St Andrews. J.M.S.S. and A.C.M. designed the study and wrote the paper with J.T.S.I.

Author Information

Correspondence and requests for materials should be addressed to A.C.M. (email: a.c.mclaughlin@abdn.ac.uk) or J.M.S.S (email: J.Skakle@abdn.ac.uk).

Additional Information

Competing Interests Statement The authors declare that they have no competing financial interests.

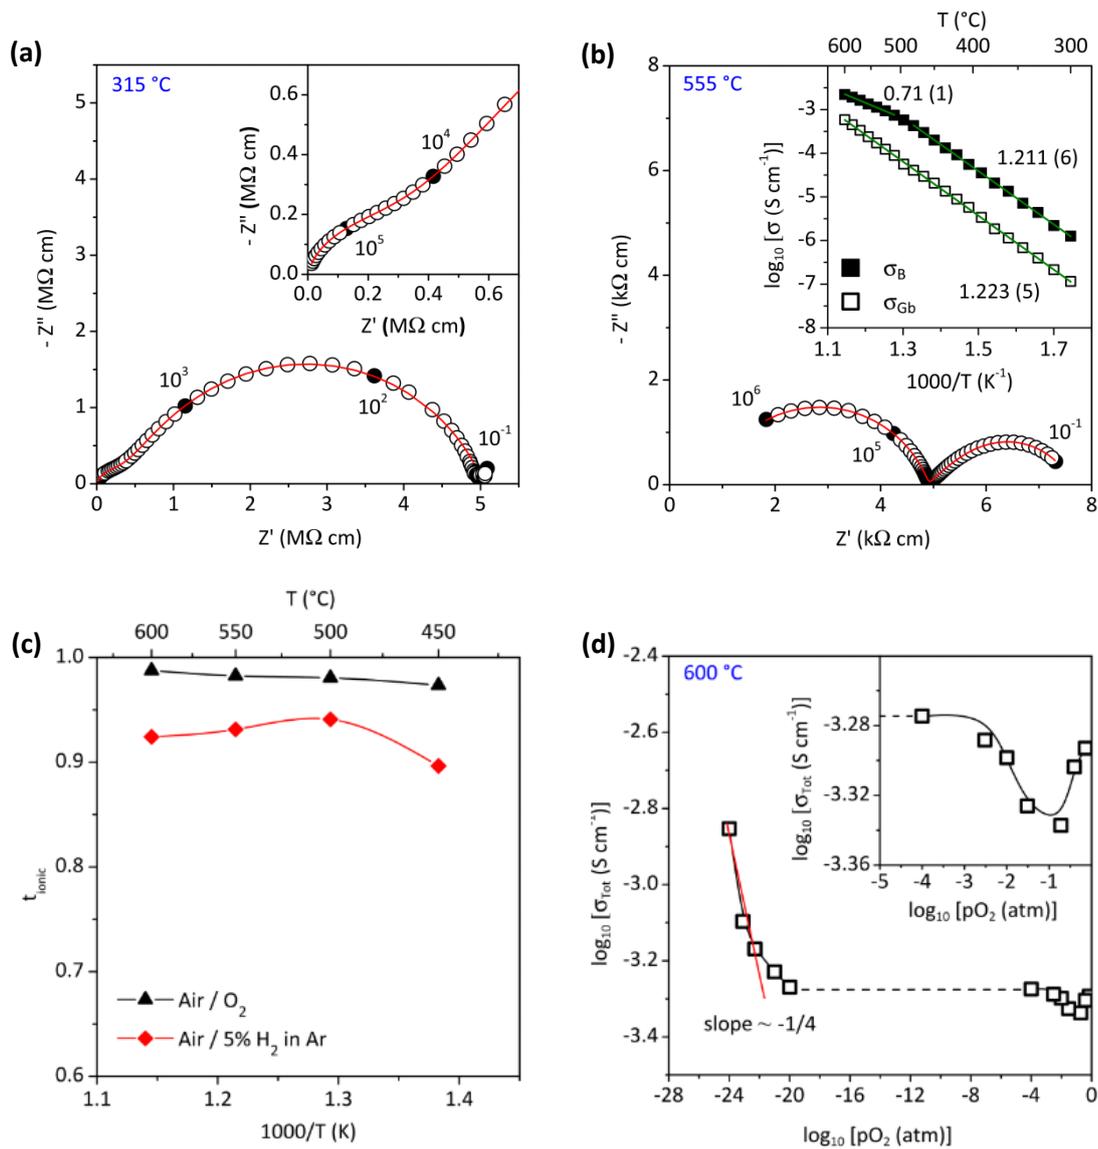


Figure 1. Ionic conductivity of $\text{Ba}_3\text{MoNbO}_{8.5}$. (a), (b) Complex impedance plots recorded in dry air at (a) $315\text{ }^\circ\text{C}$, with inset showing a magnification of the high frequency data, and (b) $555\text{ }^\circ\text{C}$, with the Arrhenius plot of the bulk and grain boundary conductivity displayed in the inset. (c) Oxygen transport number over the temperature range $450 - 600\text{ }^\circ\text{C}$ measured by the oxygen concentration cell method. (d) Dependence of the total conductivity vs pO_2 . The numbers and corresponding filled circles in (a) and (b) indicate selected frequencies (in Hz), while the red line is the equivalent circuit fitting. In the inset to (b), the green line is the linear fit to the data and the numbers are the activation energies (in eV).

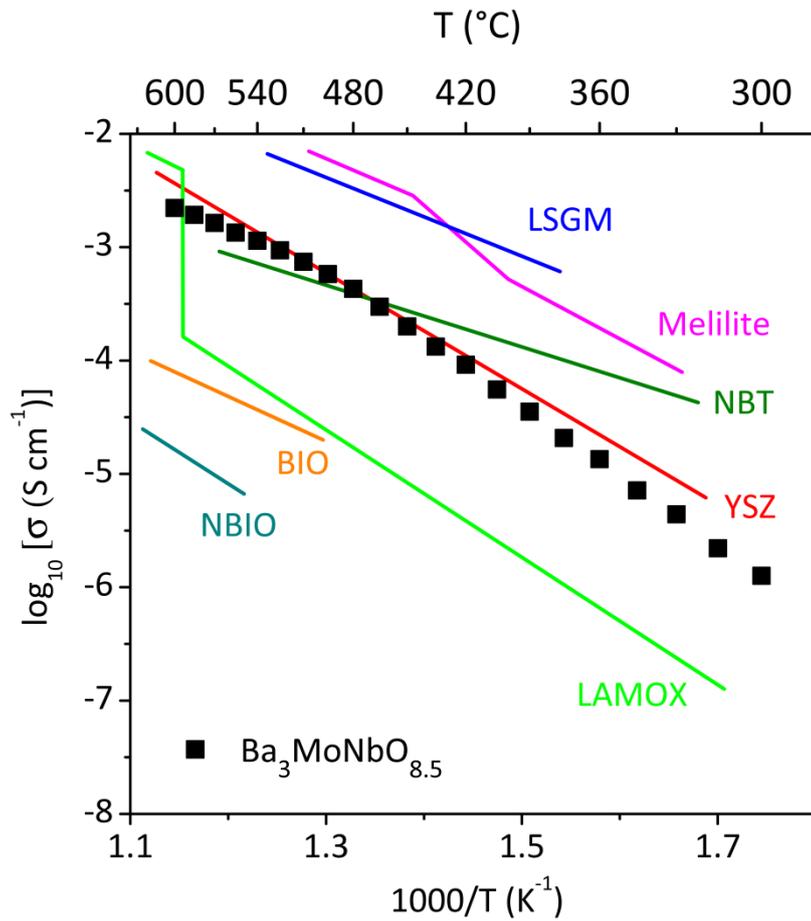


Figure 2. Comparison of bulk conductivities for $\text{Ba}_3\text{MoNbO}_{8.5}$ and other ionic conductors. Shown are $\text{Zr}_{0.92}\text{Y}_{0.08}\text{O}_{1.96}$ (YSZ, ref. 22), $\text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM, ref. 13), $\text{La}_2\text{Mo}_2\text{O}_9$ (LAMOX, ref. 7), $\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$ (NBT, ref. 8), $\text{La}_{1.54}\text{Sr}_{0.46}\text{Ga}_3\text{O}_{7.27}$ (Melilite, ref. 9), $\text{Ba}_2\text{In}_2\text{O}_5$ (BIO, ref. 23) and NdBaInO_4 (NBIO, ref. 24).

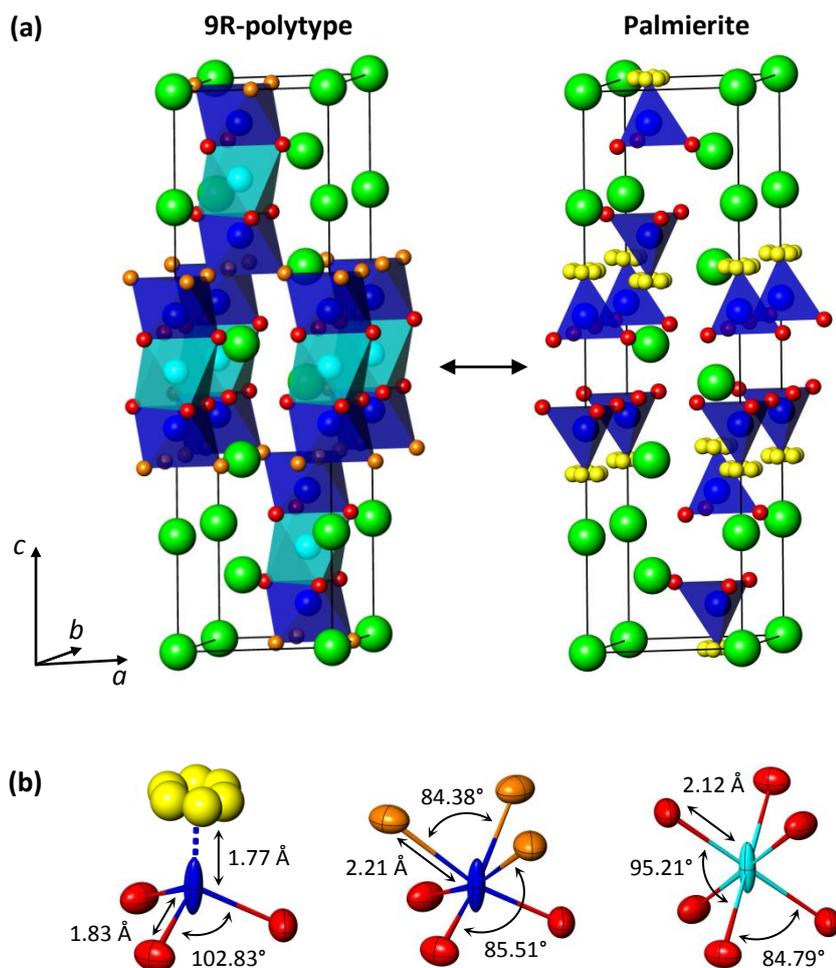


Figure 3. Crystal structure of $\text{Ba}_3\text{MoNbO}_{8.5}$. (a) The hybrid structural model formed by the superimposition of the 9R-polytype and the palmierite sub-units representing the average structure of the system. (b) Bond lengths and angles of the (Mo/Nb) O_4 tetrahedra and (Mo/Nb) O_6 octahedra, with thermal ellipsoids. Colours in (a) and (b) indicate: green Ba(1)/Ba(2), blue Mo(1)/Nb(1), cyan Mo(2)/Nb(2), red O(1), orange O(2) and yellow O(3).

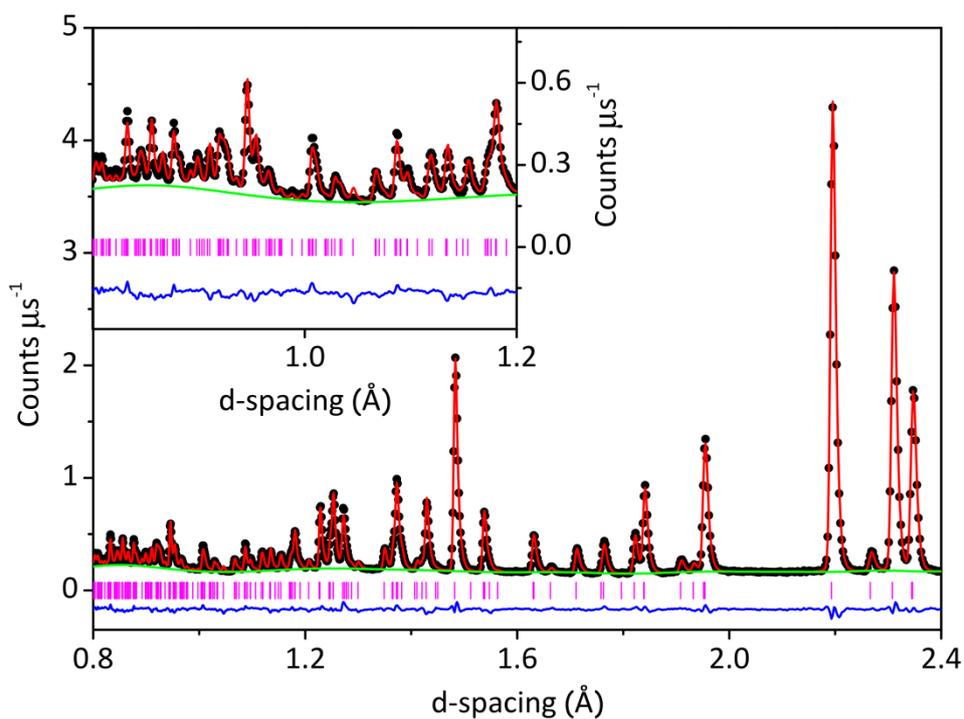


Figure 4. Rietveld refinement fit to the TOF neutron diffraction data of $\text{Ba}_3\text{MoNbO}_{8.5}$ at ambient temperature. Neutron diffraction data from the 91.5° bank detector of the GEM diffractometer is shown. Black dots indicate the observed data, the red line the Rietveld fit, the blue line the difference between the observed and the calculated patterns, the green line the background function and the pink bars are the reflection positions.

Table1. Refined atomic parameters from Rietveld fit of the powder neutron diffraction data recorded on the Gem diffractometer at 290 K. Data were refined in the space group $R\bar{3}m$ H with $a = 5.92744$ (3) Å, $c = 21.0995$ (2) Å; $\chi^2 = 2.4$, $R_p = 3.29$ % and $R_{wp} = 3.24$ %. U_{ij} indicates anisotropic thermal displacement parameters. U_{13} and U_{23} are zero due to the symmetry of the system. O(3) was refined with an isotropic thermal displacement parameter, U_{iso} .

Atom	Site	x	y	z	Occupancy	$U_{11} = U_{22}$ (Å ²)	U_{33} (Å ²)	U_{12} (Å ²)
Ba(1)	3a	0	0	0	1	0.0165 (3)	0.0192 (6)	0.0083 (2)
Ba(2)	6c	0	0	0.20629 (8)	1	0.0165 (3)	0.0192 (6)	0.0083 (2)
Mo(1)/Nb(1)	6c	0	0	0.39936 (6)	0.926 (1)	0.0049 (2)	0.0498 (9)	0.0025 (1)
Mo(2)/Nb(2)	3b	0	0	0.5	0.148 (1)	0.0049 (2)	0.0498 (9)	0.0025 (1)
O(1)	18h	0.17212 (5)	0.82788 (5)	0.10343 (2)	1	0.0215 (3)	0.0140 (3)	0.0160 (3)
O(2)	9e	0.5	0	0	0.449 (2)	0.0240 (8)	0.0121 (3)	0.0155 (4)
O(3)	36i	0.0850 (9)	0.0933 (7)	0.3195 (2)	0.096 (1)	0.0342 (2) ^b		

^b U_{iso} (in Å²).