

Waveguide Tm:Lu₂O₃ ceramic laser fabricated by ultrafast laser inscription

N. K. Stevenson^{1,3}, J. Morris^{1,2}, H. Bookey¹, A. K. Kar², C. T. A. Brown³, J. -M. Hopkins¹, M. D. Dawson^{1,4} and A. A. Lagatsky¹

¹Fraunhofer Centre for Applied Photonics, Fraunhofer UK, Technology and Innovation Centre, Glasgow, G1 1RD, UK

²School of Engineering and Physical Sciences, David Brewster Building, Heriot-Watt University, Edinburgh, EH14 4AS, UK

³SUPA, School of Physics and Astronomy, University of St Andrews, St Andrews, KY16 9SS, UK

⁴Institute of Photonics, University of Strathclyde, Technology and Innovation Centre, Glasgow, G1 1RD, UK

Ultrafast laser inscription (ULI) allows the fabrication of compact, highly-efficient and robust laser sources over a broad range of crystalline, ceramic and glass gain media. For instance, subsurface waveguides can be formed by the stress induced refractive index modification effect which takes place between two parallel modified regions referred to as “Type II” guiding [1]. Previously, a family of laser hosts known as sesquioxides, namely Lu₂O₃, Sc₂O₃ and LuScO₃, have been shown to demonstrate efficient, high-power and tunable laser operation around the 2 μ m region in both continuous-wave and pulsed regimes when doped with Tm³⁺ [2, 3]. Combining the Tm³⁺-doped sesquioxide material properties with the ULI waveguide laser geometry provides a means to produce compact, low-threshold and efficient laser sources near 2 μ m with the potential for high pulse repetition rate ultrafast operation. Here we report, to the best of our knowledge, the first demonstration of a ceramic Tm:Lu₂O₃ waveguide laser source fabricated by ULI.

The 9 mm long waveguides were fabricated in a polished 2.3×5×9 mm sample of 1 at.% Tm doped Lu₂O₃ ceramic using an ultrafast laser (Light Conversion) emitting 200 fs pulses at 500 kHz pulse repetition rate at 1040 nm. The laser beam was circularly polarised and focussed with a 0.4 NA aspheric lens 300 μ m beneath the sample surface, and the sample was translated at 5 mm/s through the focus. Type II guiding was observed in the structures inscribed at pulse energies between 0.8 μ J and 3 μ J with track separations of 20 μ m and 30 μ m. Optimal lasing performance was found for a waveguide written with 2 μ J pulses at a 30 μ m track separation.

The laser cavity was constructed with two plane dielectric mirrors mounted up against the uncoated 2.3×5 mm end facets of the sample. The input pump mirror was coated for a high reflectivity in the range of 1900 – 2100 nm and a high transmission at the pump wavelength of 795 nm, while a number of different output couplers were investigated (T=2%, 9%, 20%, 30%, 40% and 75%). The pump source was a tunable Ti:sapphire laser producing a maximum output power of 2 W at 795 nm and a polarisation orientated in the y-axis. The slightly astigmatic pump was coupled into the waveguide using a 20 mm focal length lens resulting in an average diameter spot size of 27.5 μ m. A maximum output power of 80.8 mW at 1942 nm was generated using the 40% output coupler for an absorbed power of 1.18 W (Fig. 1). A maximum slope efficiency, assuming perfect coupling, of 9.5% was achieved at optimal conditions and thresholds were observed to be in the range of 50 – 120 mW. The pump and signal modes were imaged using commercial visible and mid-IR cameras, respectively (Fig. 2). The signal mode was calculated to have a diameter of 22.5 μ m and 25.2 μ m in the x and y directions, respectively. By detuning the pump source to a non-absorbing wavelength of 860 nm, a total insertion loss for the pump was estimated to be 1.6 dB. From the laser experiments the propagation loss for the laser wavelength was estimated to be 0.99 dB/cm.

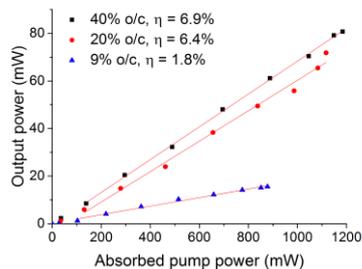


Fig. 1 Input-output characteristics of the Tm:Lu₂O₃ waveguide laser with different output couplers assuming no coupling losses.

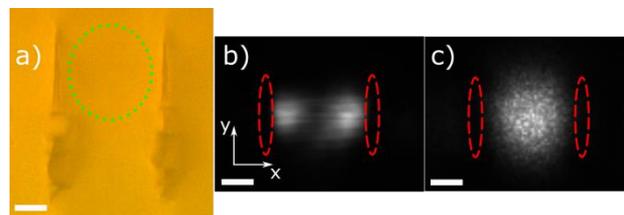


Fig. 2 a) Microscope image of a pair of tracks (separation 30 μ m, pulse energy 2 μ J). b) and c) show the pump (795 nm) and the laser (1942 nm) mode images, respectively. A 10 μ m scale bar is included. The green dotted circle shows the unmodified guiding region. Red dashed ellipses indicate the inscribed tracks.

References

- [1] D. Choudhury, J. Macdonald and A. Kar, "Ultrafast laser inscription: perspectives on future integrated applications", *Laser & Photonics Reviews* **8**, 827 (2014).
- [2] C. Kränkel, "Rare-earth-doped sesquioxides for diode-pumped high-power lasers in the 1-, 2-, and 3- μ m spectral range", *IEEE J. Sel. Top. Quantum Electron.* **21**, 1602013 (2015).
- [3] A. Lagatsky, O. Antipov and W. Sibbett, "Broadly tunable femtosecond Tm:Lu₂O₃ ceramic laser operating around 2070 nm", *Optics Express* **20**, 19349 (2012).