

Renewable Syngas & Hydrogen Synthesis via Steam Reforming of Glycerol over Ceria-Mediated Exsolved Metal Nano Catalysts

Ahmed Umar¹, Dragos Neagu and John T.S. Irvine
School of Chemistry, University of St Andrews,
North Haugh, St Andrews, Fife KY16 9ST, UK.

Abstract

Currently, catalyst design and development has drawn much attention as results of its strategic importance in the area of energy applications particular those involving biomass conversion. This work tailored exsolution of metal catalysts through the use of ceria for enhanced structural and catalytic behaviour in steam reforming of glycerol. Aside the understanding that defects due to A-site deficiency facilitates formation of vacant sites and exsolution of metal catalysts on the B-site of perovskite systems, this work has exemplified that metals such as ceria significantly influences the exsolution and general morphological surface architecture and catalytic behaviour. The exsolved nickel catalysts anchored and socketed on a titanate support and the ceria's basic surface properties and oxygen storage-release behaviour has modified the perovskite surface chemistry and enhanced catalytic behaviour particularly deactivation due to carbon deposition and reusability. Other exsolvable dopant metal species such as Fe and Co forms alloys with nickel on the surface and the synergy between the dopant metals in the alloy yielded better results. Furthermore, in one of the catalyst systems, the most commonly observed tolerable A-site deficiency and doping limit of 2% known for SrTiO₃ perovskite was overstretched by 0.5% (2.5%) thereby increasing the defect chemistry. The catalyst system with such formulation has shown a dramatic exsolution phenomenon and catalytic behaviour and robust suppression of coke deposition. CO selectivity >60% and H₂ selectivity >40% was recorded with all the catalyst systems. The catalysts used in this work are useful for applications in energy and production of value added chemicals.

Key words

Catalysis
Perovskite
Exsolution
Steam reforming
Renewable fuels
Fuel Cell

1.0 Introduction

¹ Corresponding author: u.ahmed2007@yahoo.com; ahmed.umar@uniabuja.edu.ng
Department of Chemistry, University of Abuja,
Gwagwalada, Abuja, Nigeria.

The global energy demand, environmental concerns and quest for clean energy has placed fuel cell technology at the front because of its simple practicability, energy efficiency, environmentally friendly, fuel flexibility and cost effectiveness [1-4]. The achievements recorded in fuel cell technology have shown that hydrogen driven systems would replace the fast depleting and environmentally reneging fossil-based fuel driven systems in the near future [5-7]. It is believed that the much desired renewable hydrogen fuel could be obtained through an on-board reforming of hydrogen-rich renewable biomass feedstock [8-11]. Amongst the existing reforming technologies, steam reforming has been found very efficient and quite reliable. At elevated temperatures, biomass decomposition products are steam reformed leading to the formation of gaseous products essentially, H₂, CO₂, CH₄ and CO which could be fed to fuel cell such as solid oxide fuel cells (SOFCs) as renewable fuel to the conventional fossil-based hydrogen [12-14]. Interestingly, unlike Proton-Exchange Membrane (PEM) fuel cell that sees CO as a poison to anode particularly where noble metals are involved and the fuel cell low-temperature operations, the high temperature SOFCs utilizes even CO as a fuel. With the aid of a robust catalyst system, the gaseous biomass decomposition products could be made hydrogen and carbon monoxide rich to enhance cell performance and efficiency. One of the obvious resultant problems with the use of such fuel is the degradation of fuel cell performance overtime due to coke deposition and fouling of the catalyst surface or anode material [15-17]. This called for the development of a better catalyst system that can cope with the harsh condition that ensured while using such alternative fuel.

Consequently, catalyst material remains central to steam reforming process and many of the existing technologies that are employed in biomass conversion to renewable fuels. Hence, design and development of robust and active catalyst for biomass conversion is attracting much research interest particularly perovskite materials as results of their robust structural and catalytic properties that could be enhanced or improve upon through doping [18,19]. Recently, catalyst design that involves exsolving active metal catalyst from the bulk support and decorated on an oxide support is fast gaining prominence as results of its promising catalytic properties and structural doping flexibility [20-21]. In a recent work, Umar, et al (2021) [22] has demonstrated the use of alkaline dopant metals to enhance catalytic and surface properties of exsolved nano-catalyst with perovskite structure for glycerol valorisation. The alkaline modified exsolved catalysts showed not only improved

catalytic behaviour but also reduced level of carbon deposition. It was also observed however, that nickel catalyst exsolution was very limited i.e. not properly enhanced by the alkaline metals attributed to a phenomenon called 'strontium hindrance' as reported in a related work [23,24] with a consequent reduction in the catalyst performance despite their enhanced acidic-basic surfaces. The catalyst performance suggest direct correlation between the extent or level of exsolution and the catalyst-support interaction as well as the overall catalytic activity and ability to suppress fouling of catalyst surface due to carbon deposition. Attempts were made in several related work to enhance the exsolution of metal catalyst through tailoring of reaction and reduction conditions with some promising results [20,21]. With the advances and successes recorded in the development of catalyst system through exsolution phenomenon, suffices to say supported metal catalyst design and chemistry is improved when compared the conventional method of wet impregnation.

Some nickel catalyst systems have shown some great propensity towards decomposition of biomass and hydrocarbon feedstock such as glycerol to gaseous products. However, they get deactivated easily particularly those catalyst systems prepared by wet impregnation as results massive carbon deposition, reoxidation and sintering especially when used or prepared at high temperature [25-29]. Ceria is known to enhance the reducibility of nickel and suppression of fouling of catalyst surface as a result of carbon deposition hence increasing the stability and reusability of nickel catalyst [30]. This was attributed to its enhanced catalyst-support interaction as a result of ceria's redox properties and acid-basic surface which gives it the ability to switch between its oxidation state of Ce^{+4} and Ce^{+3} . Consequently, ceria's versatility in large number of industrial processes and applications has given it economic value that has surpassed many other rare earth metals [31]. Ceria oxides-based catalyst systems are promising catalyst for many applications and were utilised as support and promoter for many catalyst systems such as automotive exhaust catalyst because of its reducibility, redox and oxygen storage-release properties as well as relative stability over varying temperatures [32-35].

Nanostructured ceria particles have been found to demonstrate relatively more impactful catalytic behaviour particularly in reforming of gaseous products for energy and environmental remediation applications [30,31]. Nanostructured nickel catalysts were tailored through the use a modifier Y_2O_3 to stabilise the nickel catalyst by

enhancing catalyst-support interaction in a ZrO_2 supported catalyst system for steam reforming of glycerol in a related work reported by Charisiou et al. 2020 [36]. The addition of the Y_2O_3 into the supported catalyst Ni/ZrO_2 did not only stabilised the catalyst but also improved the oxygen storage capacity of the support and enhanced surface chemistry of the active basic sites as well as surface particle size and population. The structured modification helped to suppress coke deposition with a resultant stabilisation and sustainability of hydrogen yield.

It is also revealed that steam reforming temperature and nature of support influences glycerol conversion and distribution of gaseous products as well as hydrogen yield. Co-based supported catalysts $\text{Co}/\text{La}_2\text{O}_3$, Co/AlZnO_x and Co/AlLaO_x prepared by incipient wetting impregnation have demonstrated high stability and suppression of coking activities attributed to the nature of the support surface chemistry [37]. The Co/AlLaO_x catalyst system was found more active, selective and more resistant to coke deposition. In related work, it is established that addition of the right amount of a catalyst modifier such as La_2O_3 to a support in a comparative study between $\text{Ni}/\text{Al}_2\text{O}_3$ and the modified $\text{Ni}/\text{La}-\text{Al}_2\text{O}_3$ enhances catalyst-support interaction, active site strength, concentration and distribution with a consequent improved catalytic activity and stability [38]. The type and nature of the carbon deposited was also influenced by the modifier. While the $\text{Ni}/\text{La}-\text{Al}_2\text{O}_3$ catalyst was associated with amorphous carbon deposited on the support that allows easy regeneration and reusability of the catalyst, $\text{Ni}/\text{Al}_2\text{O}_3$ was associated with more severe graphitic carbon deposited on the active sites. Despite the preference on the use of cheap transition and rare earth metals in the design and development of metal catalysts for steam reforming of glycerol, expensive and precious metals have also shown some promising results particularly at low reforming temperature as reported by Silva et al. 2019 [39]. However, catalyst deactivation due to rapid formation of carbon containing liquid products and deposition of amorphous carbon was observed within few hours of the test though oxidative regeneration and removal of the easy-to-remove amorphous coke has helped to enhance the catalyst reusability.

The innovative catalyst design and synthetic method of exsolution [40,41] that allows control over general morphology such as particle size and distribution and doping flexibility has opened possibilities for tailoring and fine tuning structural properties for diversified morphological architecture in order to achieve the much desired robust

catalyst systems for different applications [40-45]. In this work the influences of A-site dopant metal (ceria) and lattice defect on the exsolution of catalyst nanoparticles in the B-site of perovskite and catalytic behaviour of the systems in relation to steam reforming of glycerol is reported. Particularly, ceria was selected to demonstrate its influences and mediation in the exsolution process and compared to some metal such as alkaline metals. The aim was to generate syngas as well as hydrogen gas from the low cost, readily available and renewable glycerol from biodiesel synthesis as alternative, renewable fuel for the utilization of solid oxide fuel cells and for production of other value-added chemicals. It is also believed that catalytic conversion of CO₂ and CH₄ (major contributors to greenhouse effect) to CO and H₂ (syngas) through dry reforming and steam reforming will limit their environmental effects (global warming). Series of ceria containing non-stoichiometric titanate perovskite catalyst systems were designed and tailored to be A-site deficient to mediate and facilitate the exsolution of the B-site nickel catalyst, enhance basic properties, catalyst-support interaction and other catalytic behaviour as well as suppression of carbon deposition. Possible formation of alloyed catalyst systems between the exsolved metals (Ni, Fe, Co) and innovative synergic effect on the catalytic behaviour in relation to steam of glycerol was also investigated. It is also to demonstrate the structural stability and exsolution of nano catalyst, selectivity for the desired products and ability to suppress catalyst deactivation as a results of carbon deposition that is associated with overstretched highly oxygen deficient perovskite catalyst with A-site deficiency of 2.5% in one of the formulations as against the known tolerable A-site deficiency and doping limit of 2% of SrTiO₃ type perovskite.

2.0 Materials and Methods

2.1 Catalyst synthesis and processing

The catalysts were prepared using modified solid state synthesis as described by Umar et al (2021) [22]. In this method, required weight of dried oxides of metals and carbonates was dried at elevated temperatures of 300-800 °C were measured while hot (at 300 °C) and mixed in a beaker along with the required weight of nitrate of some metals as specified in the catalyst formulation. Hypermer KD-1 (polyester/polyamide copolymer) dispersant was added to the mixture to improve dispersion and suppress agglomeration. Acetone was added to the mixture and homogenised using ultrasonic probe and eventually dried on hot plate then

calcination at 1000 °C. Further calcination was carried out at 1400-1430 °C to obtain the ready-made or as-prepared/pre-reacted samples of the catalyst systems.

To obtain the exsolved nano catalysts, the ready-made catalysts were subjected to reduction process at 900 °C in tubular furnace for 30 hours under 5% H₂/Ar mixture. The synthesised materials are: La_{0.7}Ce_{0.1}Fe_{0.3}Ni_{0.1}Ti_{0.6}O_{3-δ}, La_{0.8}Ce_{0.1}Ni_{0.4}Ti_{0.6}O_{3-δ}, La_{0.6}Ce_{0.05}Sr_{0.1}Ni_{0.1}Ti_{0.9}O_{3-δ} and La_{0.7}Ce_{0.1}Co_{0.3}Ni_{0.1}Ti_{0.6}O_{3-δ} respectively.

2.2 Catalyst Characterization

Room temperature crystallographic data were collected on Pan-Analytical Empyrean X-Ray Diffractometer (XRD) operating on reflection mode using Cu-Kα₁ radiation at λ = 1.5406 Å and 10-90 2θ angle range for 1 hour.

Surface area, pore volume and size determination were carried out by Brunauer-Emmitt-Teller (BET) and Barrette-Joyner-Halenda (BJH) methods respectively using nitrogen adsorption/desorption at 77.35K using Micrometrics TriStar II 3020 model. Before the analysis, samples were heated for 3 hours at 120 °C to remove moisture and other residual gases.

Morphology and surface properties of the catalyst were investigated using Field Emission Scanning Electron Microscopy (FESEM) JEOL JSM6700F.

Thermo-gravimetric Analysis using NETZSCH TG 209 analyser was used to investigate reducibility and thermal stability of the materials. Each sample was run in air/argon mixture to 900 °C at heating rate of 3°/min in aluminium crucible, after cooling, the sample was then run in reducing environment using 5%H₂/Argon mixture to same temperature.

Coking activities resulting to carbon deposition from the catalysis process on the used catalyst surface was characterized using temperature programmed oxidation (TPO) on NETZSCH STA 449C thermogravimetric analyser equipped with thermstar mass spectrometer. Specific weight of the spent catalyst was taken into the thermogravimetric analyser and argon gas was used to flush the system residual gases in the system. Surface carbon was oxidised to CO₂ using O₂ to temperatures of 900 °C. Gases produced were trapped and channelled for analysis using mass spectrometer.

2.3 Catalytic gasification and steam reforming testing

A fixed bed in a quartz tube reactor (8 mm internal diameter (ID), 10mm outer diameter (OD) and 24cm long) was used for run steam reforming catalysis of pure glycerol at 700 °C and atmospheric pressure. The schematic diagram of the reactor assembly and details of the procedure is as shown and described in Umar, et al (2021) [22].

3.0 Results and Discussion

3.1 Catalyst Characterization

3.1.1 CRYSTALLOGRAPHIC DATA AND ANALYSIS

The room temperature X-ray Diffraction pattern of the materials shown in Figure 1 was collected and used to characterize the phase purity of the synthesised catalyst materials; $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ (LCeFNT), $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ (LCeNT), $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ (LCeSrNT) and $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ (LCeCoNT) respectively. The A-site deficient materials were designed to have different vacancies and dopant materials for comparison. Analysis by Indexing of the XRD pattern as shown in Figure 1a and b confirms that all the reflections or peaks in the pattern peaks or are typical of perovskite structure [42,46,18] suggesting successful synthesis of pure and single phase perovskite materials except $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ which showed some anomalous behaviour as explained below.

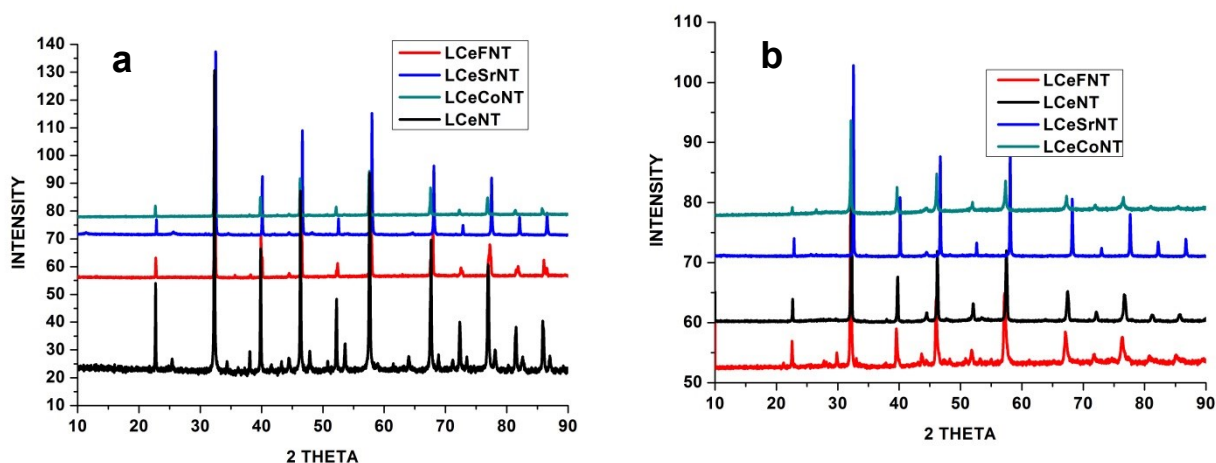


Figure 1: The XRD patterns of the synthesized A-site deficient nickel-based titanate perovskites of the samples showing their phase purity **a**, for the as prepared samples prior to reduction and **b**, the reduced samples showing them maintain their perovskite structure with no evidence of decomposition or disintegration after reduction for 30 hours at 900 °C in hydrogen.


It is interesting to note that the $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ perovskite with 25% ($\alpha=0.25$) A-site deficiency was also successfully synthesized. There is no evidence of formation of new or extra phase in the XRD patterns. This new material particularly has demonstrated a robust exsolution of nickel nanoparticles well distributed on its surface as seen in Figure 5. Rietveld refinement of the XRD patterns of the materials before reduction revealed different symmetry and space groups for the as-prepared materials as shown in Table 1.

| Catalyst | Abbreviation | Space group | Cell Parameter | Cell Volume | Refinement fit parameter |
|---|--------------|---------------|-------------------------------------|-------------|--|
| $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ | LCeNT | <i>Pbnm</i> | a= 5.5452 b= 5.5329 c= 7.8221 | 239.992 | $R_p=6.82$, $R_{wp}= 9.54$, $R_{Exp}=12.14$, $X^2=0.619$ |
| $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ | LCeSrNT | <i>I4/mcm</i> | a= 5.5025 b= 5.5025 c= 7.7820 | 235.622 | $R_p=10.2$, $R_{wp}= 13.8$, $R_{Exp}=7.92$, $X^2=3.05$ |
| $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ | LCeCoNT | <i>I2/a</i> | a= 7.8459 b= 5.5408 c= 5.4007 | 240.543 | $R_p=7.24$, $R_{wp}= 9.54$, $R_{Exp}=8.54$, $X^2=1.25$ |
| $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ | LCeFNT | - | - | - | - |

The overlaid patterns shows a slight shift in the 2θ position revealing the influence of the differences in ionic size among the dopant ions used and changes associated with structural symmetries shown by the samples in the refinement data of Table 1. The stability of the reduced samples in hydrogen atmosphere and maintenance of their perovskite structure after prolong reduction for 30 hours at 900 °C is also supported by the XRD patterns of Figure 1b when compared to other materials that decomposes in reducing atmosphere at elevated temperatures [47,48]. This is further corroborated by the thermogravimetric analysis shown in Figure 4. There is also evidence of reduction in the intensity of the perovskite peaks or complete disappearance after reduction when compared to that of the original sample XRD pattern before reduction and the splitting pattern of the peaks is also noticeably less. This observation becomes more apparent in $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ perovskite which

shows fewer peaks in Figure 1b compared to the more seen on the XRD pattern of Figure 1a above before reduction which suggests evolution to higher symmetry by the reduced materials. There increase in d-spacing as suggested by shift to smaller 2θ angles also resulting from increase in volume of the unit cell caused by the redox behaviour of titania's transformation from smaller Ti^{4+} ions to larger Ti^{3+} during electronic transfer influence by reducing atmosphere.

Table 1: Summary of the refinement data
 The Rietveld refinement data in Table 1 shows that space group, lattice parameter 'a' and the cell volume varies among the perovskite materials synthesised in this work reflecting the different dopant and level of defect due to A-site deficiency. The original patterns have shown good matching and correlation with the refinement crystal model and the proposed space groups as seen in Figure 2a-c. The crystal model also shows the orientation of the atoms in space and octahedral distortions i.e. in-out-of-phase tilting in the same Figure 2a-c. It is interesting to note that despite all the samples contains ceria, they all exhibited different symmetry and distortions which is clear manifestation of the influence of the varying other dopants used and A-site deficiency amongst the catalyst systems. The space group and structural model suggests distortions along all the crystallographic axes and seen Figure 2a-c.

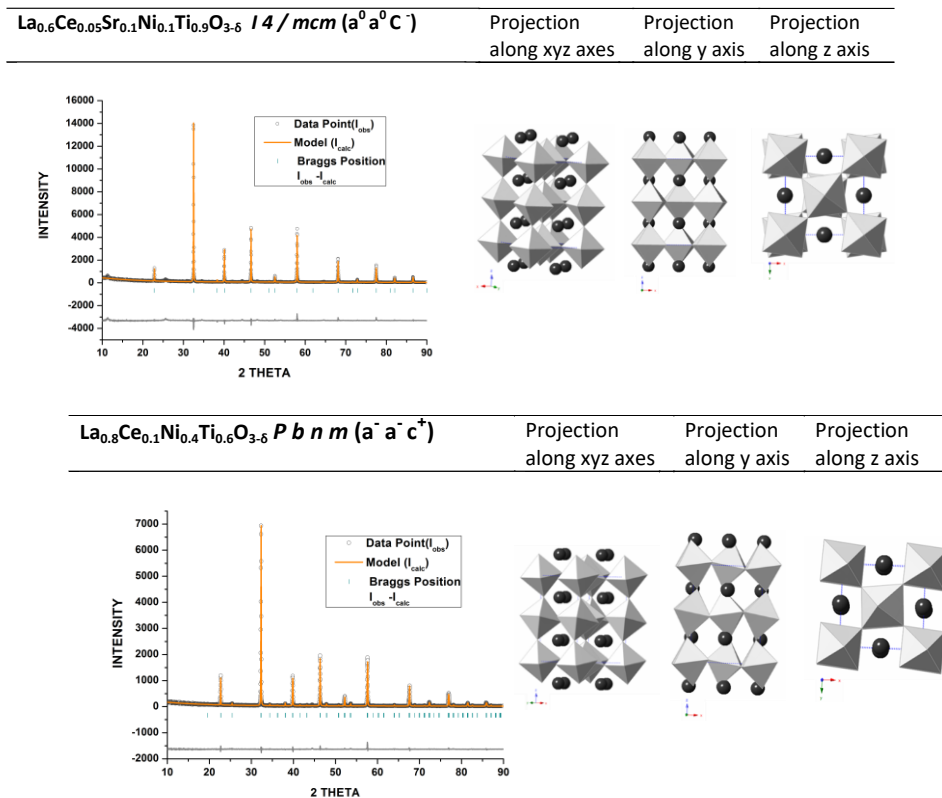

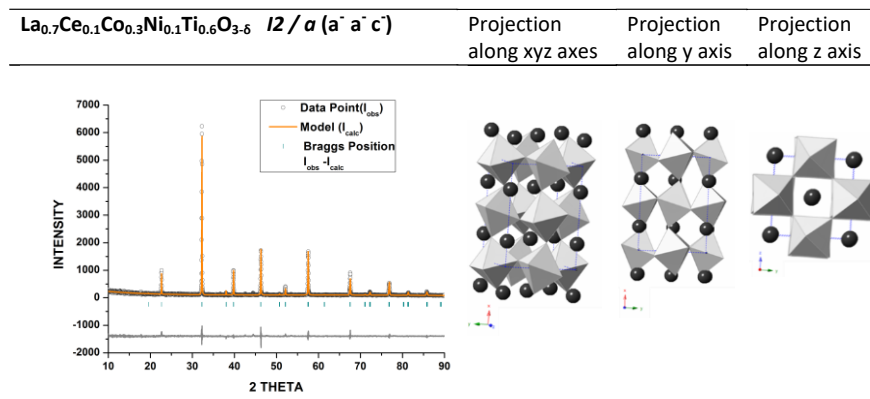


Figure 2: The proposed tetragonal model matching with the XRD pattern of the synthesised materials and the projection of the structure showing out-of-phase tilting along z -axis as the $I4/mcm$ space group suggest in **a**, $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ and out-of-phase tilting along x and y axis but in-phase tilting along x axis as the $pbnm$ space group suggest in **b**, $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ and **c**, $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ shows out-of-phase tilting along all the axes as the $I2/a$ space group suggests.

The refinement process administered on the $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ sample was not complete or successful as a result of the apparent complexity associated with its structure. Many attempts were made and the entire space groups proposed could not match or fit it accurately. The peaks splitting pattern observed for this particular material is not known to perovskite structure as exemplified in Figure 3. These uncommon splitting pattern of $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ sample peaks was traced to a possible formation of two perovskites super imposed in one another and hence could not fit or match a specific structural model used for it.

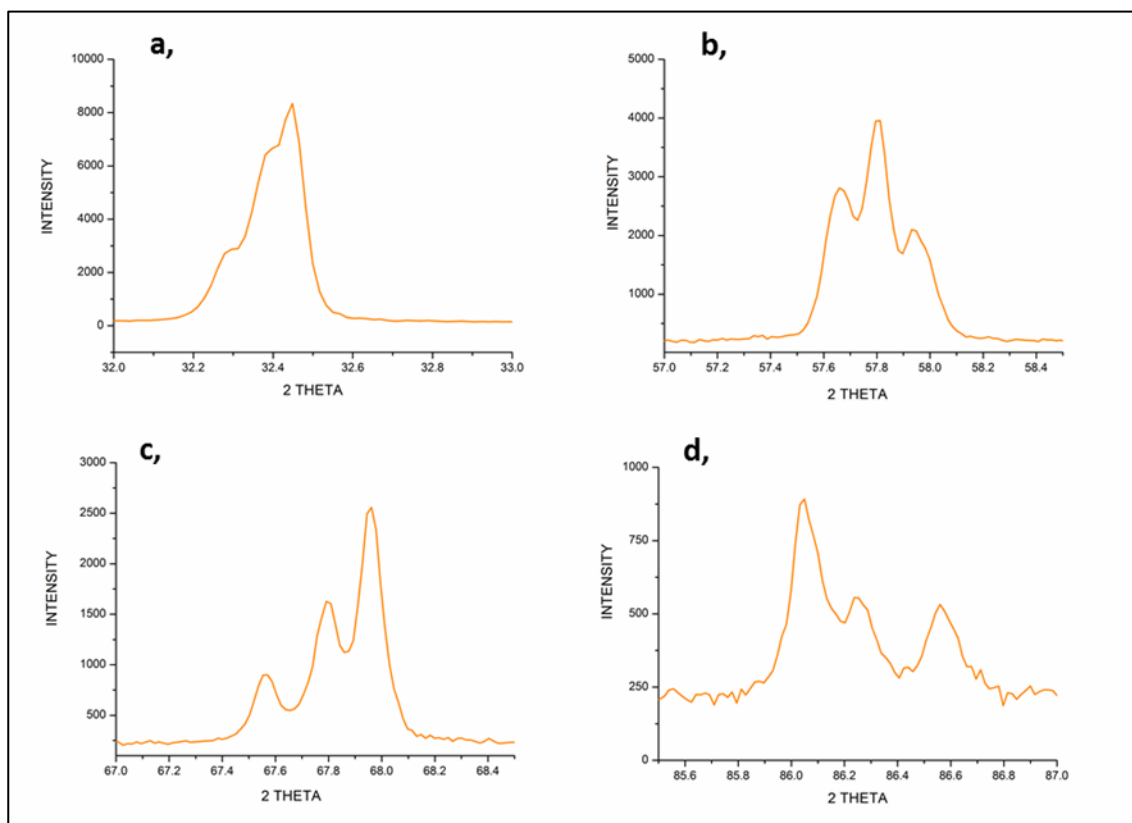


Figure 3 Is showing the multiple splitting pattern of peaks from the $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3\pm\delta}$ catalyst XRD. The peaks corresponds to the following hkl values **a**, 220 **b**, 422 **c**, 440 and **d**, 444 respectively.

3.1.2 STABILITY OF THE NICKEL-BASED A-SITE DEFICIENT SAMPLES BY THERMO-GRAVIMETRIC INVESTIGATION IN AIR AND HYDROGEN

Thermal stability and stability of the materials in air and hydrogen atmosphere was investigated via thermo-gravimetric method of analysis and the results obtained are as shown in Figure 4a and b. The Figure 4a shows the TGA profile of the as prepared samples. The TGA profile as denoted by the segmented dotted line shows oxidation in air and reduction in hydrogen atmosphere respectively. In Figure 4a, all the materials have shown consistent and persistent thermal stability in air atmosphere at all temperatures under study hence showed no evidence of weight loss or gain. In the reduction process as shown in the second segment of Figure 4a, weight loss of about 1.36% (0.5 mg) in the hydrogen atmosphere was observed for $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ catalyst. There is also a slight weight loss due to $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ with 2.5% A-site deficiency and a little corresponding weight loss of about 0.7% (0.29 mg) from $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ containing Co.

The XRD pattern of these compounds in Figure 1b showed no evidence of decomposition of these materials or segregation in the hydrogen atmosphere hence these weight losses are partly attributable to the oxygen storage-release properties of ceria.

Figure 4b shows the TGA profile of the reduced samples in air and hydrogen respectively as also shown by the dotted line of Figure 4b. There is a weight gain by the ceria-containing samples in air which is attributable to gain of oxygen by the highly reduced samples. Similar trend of weight loss due to oxygen loss during reduction is evident in the second segment of the TGA profile. Essentially, $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ profile stood out distinctively in both segments showing a large weight gain of about 2.87% (1.33 mg) and 2.01% (0.72 mg) weight loss. $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ also showed similar trend, recording a weight loss of 1.39% (0.64 mg) and gain of 2.60 % (1.19 mg). The ceria's oxygen storage-release properties might be partly responsible and the additional contribution due to the redox active Fe in $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ gave that compound an edge over the rest materials.

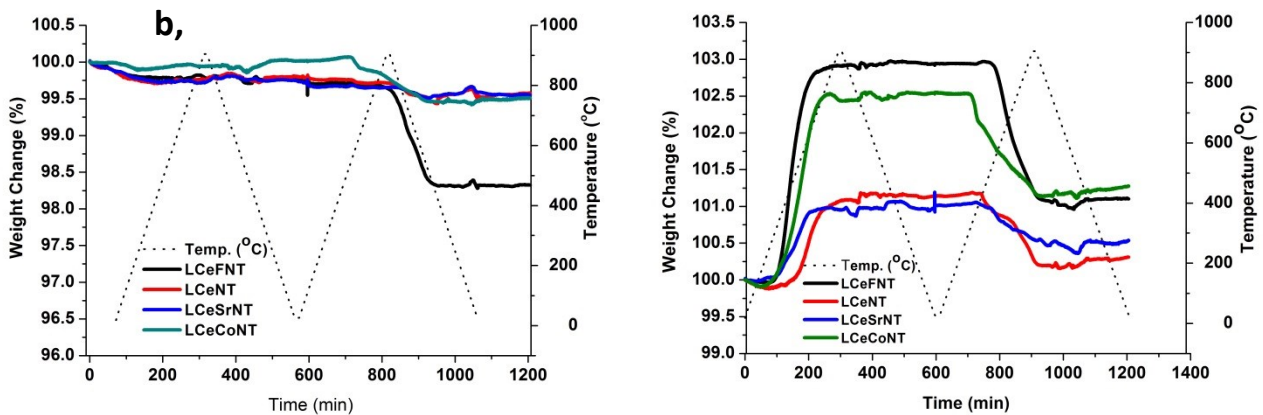


Figure 4: Thermo-gravimetric analysis showing stability of the samples in both air and hydrogen atmosphere heated to 900°C at heating rate of 3°/min **a**, TGA of the as-prepared samples before exsolution by reduction. The first segment of the denoted line shows oxidation in air and the second segment of the dotted line shows reduction in hydrogen **b**, TGA of the reduced samples after exsolution. The first dotted segment shows oxidation of the samples in air and the second reduction in hydrogen atmospheres respectively.

To strengthen this observation further, the TGA profile $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ doped with only 5% ceria when compared to the 10% in others yielded the lowest weight losses though its highest titania content that is so redox inactive would have

influenced the observed trend. It is evident from the XRD pattern of the reduced samples as explained above; these weight changes are attributable to oxygen storage-release properties of ceria and not segregation or decomposition of these samples [49,18]. These observations support the thermal stability and structural integrity of these perovskite materials in air and hydrogen. Furthermore, suffices to observe that integration of other dopant metals in these formulations have strengthened the thermal and structural stability of ceria to high temperature operations [30, 3,47,19]. Consequently, tailoring oxygen storage-release property of perovskite material could help to improve oxygen ion mobility and catalytic properties for enhanced oxidation of gassified biomass decomposition of products particularly carbonaceous species that could deactivate catalyst surfaces and facilitate product dissemination.

3.1.3 PHYSICOCHEMICAL PROPERTIES

Surface area, pore size and volumes of the solid state synthesized nickel-based titanates were investigated and results of the analysis are shown in Table 2. High temperature solid state reaction temperatures of 1430 °C was used for the synthesis and reduced in 5% H_2 at 900 °C for 30 hours in a tube furnace. The results show an increase in the surface area of the materials after reduction. The surface exsolution has transformed surface general morphology as seen in the SEM micrographs in Figure 5 with catalyst particles uniformly distributed on the surface instead of getting imbedded in the bulk leading to the observed increase in surface area. Perovskite materials naturally exhibit naturally poor surface area because they are conventional synthesized at higher temperatures (800-1500 °C) [50,51] and the results in this work suggest exsolution as a method of synthesis could be used to enhance the poor surface area of perovskite materials [20,52], and the results is favourably comparable to the use of templating agents [53,54]. The reduction process resulted in nickel particles and other dopants (Fe and Co and their alloy) exposed to the surface and dispersed uniformly across the surface as a result of exsolution with consequent increase in surface area for robust catalytic behaviour.

Table 2: Physicochemical Properties

| Catalyst Systems | A-Site deficiency | Surface Area before Reduction (m ² /g) | Surface Area After Reduction (m ² /g) |
|---|-------------------|---|--|
| La _{0.7} Ce _{0.1} Fe _{0.3} Ni _{0.1} Ti _{0.6} O _{3-δ} | 20 | 3.88 | 5.65 |
| La _{0.8} Ce _{0.1} Ni _{0.4} Ti _{0.6} O _{3-δ} | 10 | 2.37 | 3.81 |
| La _{0.6} Ce _{0.05} Sr _{0.1} Ni _{0.1} Ti _{0.9} O _{3-δ} | 25 | 2.21 | 3.91 |
| La _{0.7} Ce _{0.1} Co _{0.3} Ni _{0.1} Ti _{0.6} O _{3-δ} | 20 | 2.27 | 4.82 |

Generally, though the surface area is not large enough and that there is no consistent or conclusive correlation between the surface area observed among the materials and the defect due to A-site deficiency, it is observable that materials have shown improved surface area and robust active sites that could enhance catalytic activity when compared to other perovskite catalyst systems that are not exsolved.

3.1.4 MICROSTRUCTURE OF THE EXSOLVED NANO CATALYSTS

The SEM micrograph of the exsolved nanoparticle of the catalysts as shown in Figure 5a-f revealed transformation of the surface morphology covered by well distributed oxide-supported metal nanoparticles grown from the host perovskite structure. The dotted and dispersed particles are largely nickel nanoparticles, some Fe, Co or Ni-Fe and Ni-Co alloys resulting from the exsolution phenomenon arising from the migration of oxygen ion in the bulk to the surface due to imbalance that removal of surface oxygen during the reduction process have created. Consequently, to balance such non-stoichiometry and instability, expulsion of metals occurs from the non-defective B-site onto the surface anchored and supported on the titania oxide [42,45]. It is evident in the micrograph images that the expelled nanoparticle catalysts are largely anchored and socketed on the outer surface of the materials rather than in the bulk. These transformations have exposed the active sites to the surface for more effective catalysis process and have also naturally improved catalyst-support interaction and enhanced reducibility of nickel catalyst [22,23].

The SEM micrograph in Figure 5a-g shows that individual formulation responds differently to the reduction process and the exsolution. The ceria containing materials (Figure 5a-d) shows a good exsolution when compared to non-ceria containing material (Figure 5e-g). This shows that choice of dopant metal on the A-site of the perovskite material could be tailored to enhance migration of metal catalyst from the B-site onto the surface (exsolution) to enhance structural and catalytic properties [42,45]. Although the behaviour of the material is attributed to the constituent dopant

or metal, the defect due to A-site deficiency has played an important role. For instance, comparing $\text{La}_{0.4}\text{Sr}_{0.2}\text{Ca}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ (Figure 5f) and $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ (Figure 5c), it is evident the replacement of calcium with ceria has suppressed the so-called 'Sr hindrance' believed to hinder exsolution of Ni in $\text{La}_{0.4}\text{Sr}_{0.2}\text{Ca}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ and also reported in a related work by Neagu et al., (2015) [23] and Umar et al., (2021) [22]. Similarly, the combined influences of defect due to A-site deficiency and choice of dopant metals clearly manifests when comparing $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ (Figure 5b) and $\text{La}_{0.5}\text{Sr}_{0.4}\text{Fe}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.8}\text{O}_{3-\delta}$ (Figure 5e). Furthermore the $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ catalyst system with 25% A-site deficiency was better excluded than $\text{La}_{0.4}\text{Sr}_{0.2}\text{Ca}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ and $\text{La}_{0.8}\text{Ca}_{0.1}\text{Cr}_{0.2}\text{Ni}_{0.2}\text{Ti}_{0.6}\text{O}_{3\pm\delta}$ with only 10% A-site deficiency. In addition to introducing ceria, increasing deficiency and defect also increases ion mobility within the systems [55,56,18]. More so, all the four samples containing ceria (a, b, c and d) have demonstrated better exsolution and uniform dispersion of B-site cations compared to non-ceria containing materials (e, f and g) that showed limited exsolution of nanoparticles.

Interestingly, the new material $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ (Figure 4c) with the 25% A-site deficiency, apart from exhibiting excellent exsolution behaviour with nickel nanoparticles dispersed uniformly on its surface, the TGA analysis of the sample before and after reduction as seen in Figure 3 has confirmed the relative redox stability of this sample as no evidence of possible decomposition or segregation was noticed on the TGA profile. The observation is corroborated by the XRD pattern of the sample after reduction as seen in Figure 1 above. This is against the consequent decomposition or segregation of the constituent atom that happens when the limit of deficiency or excess is exceeded. This goes to show that the deficiency or excess could be stretched with no apparent damage to the structural integrity or stability of the sample provided the right constituent dopants tolerant of that situation are selected and used in a suitable ratio. Consequently, tailoring A-site deficiency and choice of constituent dopant metal could help in catalyst design to significantly transform surface morphology such as exsolution and distribution of nanoparticle metal catalysts for improved for enhanced and robust catalytic activity or behaviour.

| | | |
|--|---|--|
| a , $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ | b , $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ | c , $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ |
|--|---|--|


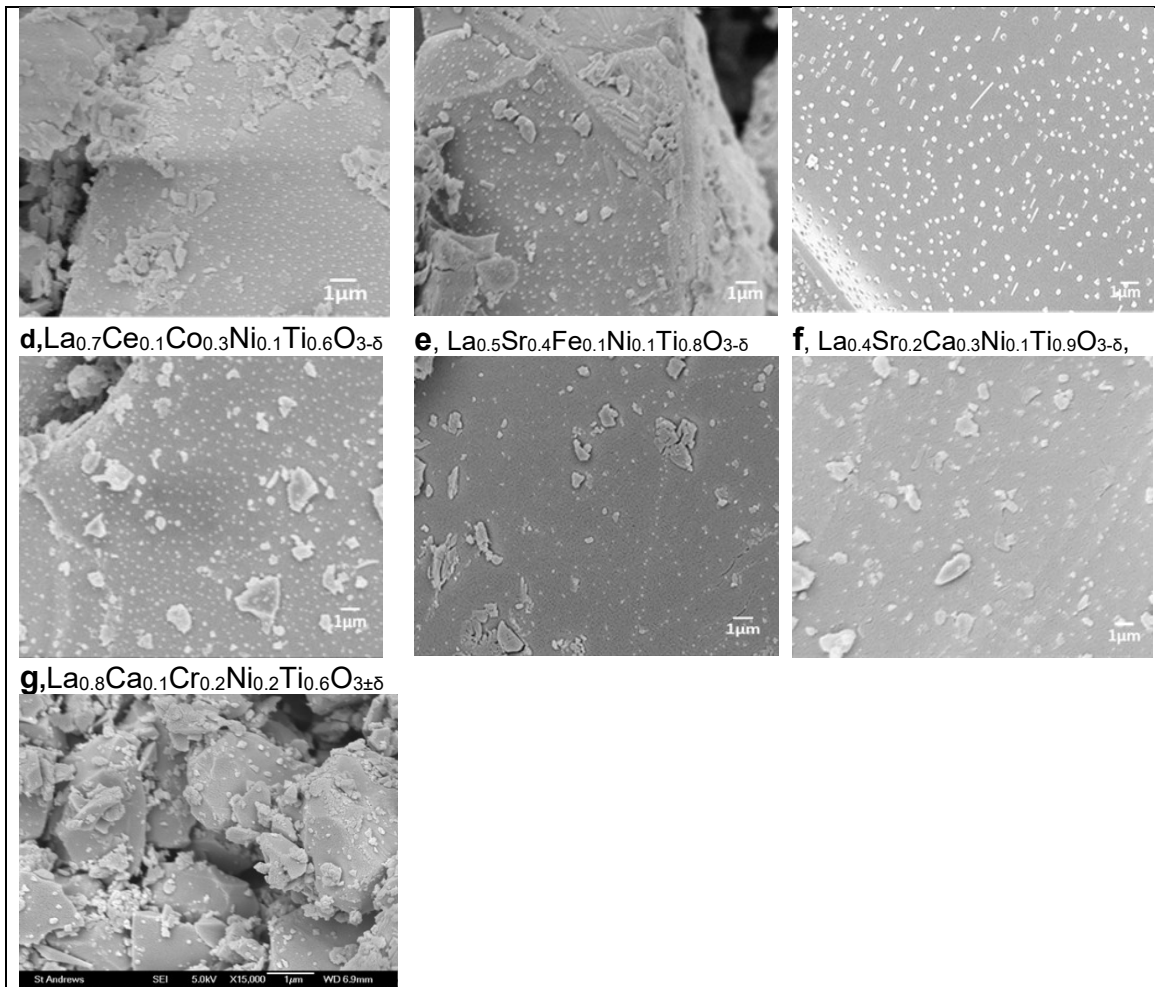


Figure 5 Micrograph of the A-site deficient titanates showing exsolved metal particles in **a**, $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$, **b**, $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$, **c**, $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ **d**, $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$, **e**, $\text{La}_{0.5}\text{Sr}_{0.4}\text{Fe}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.8}\text{O}_{3-\delta}$, **f**, $\text{La}_{0.4}\text{Sr}_{0.2}\text{Ca}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ and **g** $\text{La}_{0.8}\text{Ca}_{0.1}\text{Cr}_{0.2}\text{Ni}_{0.2}\text{Ti}_{0.6}\text{O}_{3\pm\delta}$

3.2 Catalytic activity and selectivity of the materials for the gaseous products

To evaluate the catalyst behaviour and activity, catalytic test was carried out at 700 °C using pure glycerol at atmospheric pressure and steam-to-carbon ratio of 1:3 on 50mg catalyst amount. 2.60×10^{-4} mole/min molar flow rate of glycerol-water solution and WHSV of 28 h^{-1} was maintained throughout the duration of the test. The aim was to generate stream of syngas or hydrogen gas for utilization in solid oxide fuel cell as alternative renewable fuel to the conventional fossil-

a,

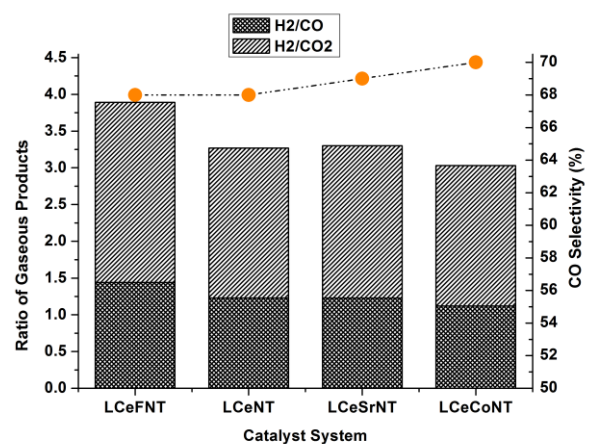

b,

based hydrogen or production of other value added chemicals. The results of the test as presented in Figure 6a shows catalytic activity in terms of stream of gases generated in mole/mole of glycerol against hydrogen selectivity.





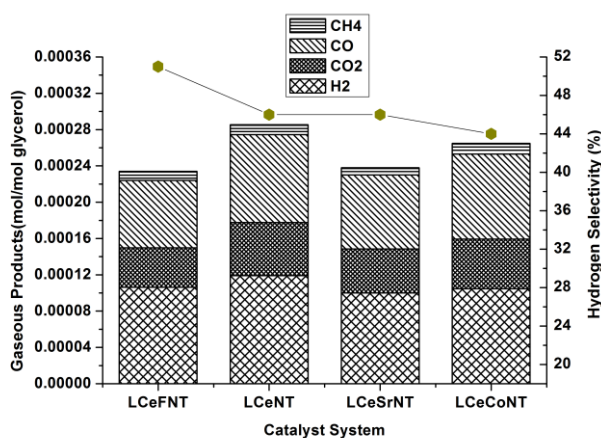


Figure 6a, Catalyst performance evaluation showing catalytic activity as gaseous products produced in mol/mol in comparison with hydrogen selectivity. **b**, Ratio of the gaseous product in relation to CO selectivity

The steam reforming results show that the catalyst systems are active and selective to the gaseous species H₂, CO₂, CO and CH₄ detected during

the analysis with H₂ and CO appearing as are the predominant gases produced with all the catalyst systems as related work shows [36]. The H₂/CO₂, H₂/CO ratios and high CO selectivity relatively of Figure 6b as well as high hydrogen selectivity in Figure 6a all attests to these observations. The analysis in Figure 6b show a high value of H₂/CO₂ than H₂/CO which suggests more CO was produced than CO₂. This is attributable to the catalyst effective gasification and oxidation of the glycerol decomposition carbonaceous products via reactions such as reverse water gas shift reaction (RWGSR) and glycerol rapid pyrolysis due to kinetics and nickel contents as exemplified in the equations (Eqn1-4) provided below.



The catalyst performance is corroborated by the excellent suppression of carbon deposition reported in Figure 8. Another important contributor to large production of H₂ and CO is the combination of dry reforming of methane (DRM) (Eqn5) and steam reforming of methane (SRM)(Eqn6) reactions catalysed by the catalysts used in this test.



Figure 5a shows a limited production of CH₄ and CO₂ which suggests the catalyst systems actively catalysed these reactions to produce large syngas with robust suppression of carbon deposition as supported by the analysis in Figure 8. These results and observations enhances industrial applicability of DRM with these catalyst systems since carbon deposition and sintering were identified as the major problems associated with the use of DRM in practical industrial applications [31]. The large synthesis gas produced could be utilised not only in fuel cell technology but also in production of other value-added chemicals and in Fischer-Tropsch process for the production of long-chain hydrocarbons and oxygenate renewable chemicals [30,31]. The test result also shows that the catalyst could be used to remove or reduce the concentration CH₄ and CO₂ as main agents of global warming from the environment via DRM and SRM. Considering the amount of catalyst used (50mg) in this test, the catalyst samples gave a reasonable conversion to gaseous products with a good selectivity for H₂ and CO comparable to other reported work [16,31,18,] despite limiting factors such as water gas shift reaction, formation of acrolein and carbonyl compounds and too much through put due to small catalyst bed that might have influenced the desired products yield.

From the test so far carried out in this work, one cannot correlate defect due to A-site deficiency to the observed performance conclusively. However, it is observable that the high CO selectivity >60% and H₂ selectivity >40% recorded virtually with all the samples could be attributed to enhanced oxidation of the carbon containing residues by the catalyst due to good oxygen mobility in them as results of their A-site deficiency defect as well as oxygen storage-release properties of the dopant ceria[43,45,]. The basic-acidic properties of ceria and alkaline dopants used in some is also an important parameter [22, 30,32,38]. Therefore defect chemistry due to A-site deficiency and choice of doping metals for both A-site and B-site could be tailored to improve B-site metal catalyst exsolution for biomass conversion to renewable hydrogen and syngas.

It is important to observe that surface area of the ceramic materials influences the concentration or amount of exsolved nano catalyst and has contributed to the observed catalytic activity or behaviour of the catalyst systems. The trend of catalytic activity in relation to generation and distribution of stream gaseous products as shown in Figure 6a is a clear manifestation of the trend of surface area of both the ceramic materials before reduction and the exsolved materials after reduction as seen

in Table 2. Catalysis been a surface phenomenon is influenced by the surface area of perovskite ceramics [18,38]. The results of the catalysts test have demonstrated that the amount of exsolved catalysts is related to the surface area of the original perovskite material and so also catalytic activity.

3.3 Stability of the catalyst systems to prolong usage against deactivation

The catalysts systems were subjected to long hours of testing to further analyse their activity and stability to agents of deactivation such as carbon deposition, sintering and catalyst poisoning due to prolonged usage in gaseous stream. The performance was investigated by monitoring hydrogen production per mole of glycerol over time for 10 hours. The test was carried out using continuous flow of pure glycerol-water mixture at 700 °C and steam-to-carbon ratio of 3:1 at atmospheric pressure. WHSV of 28 h⁻¹ was maintained throughout the duration of the test and result obtained is as shown in Figure 7. The catalyst systems have shown consistent production of hydrogen with no evidence of much loss of activity. This observation suggests remarkable resistance to catalyst deactivation as no evidence of much or serious loss of performance was recorded. The La_{0.8}Ce_{0.1}Ni_{0.4}Ti_{0.6}O_{3-δ} despite its initial good performance, the hydrogen yield reduced rapidly within two hours of the test before stabilizing. Both La_{0.7}Ce_{0.1}Fe_{0.3}Ni_{0.1}Ti_{0.6}O_{3-δ} and La_{0.6}Ce_{0.05}Sr_{0.1}Ni_{0.1}Ti_{0.9}O_{3-δ} showed similar trend. The drop in hydrogen production is attributed to the intense catalytic activity they attracted to their surfaces. Nonetheless, the stability of the La_{0.6}Ce_{0.05}Sr_{0.1}Ni_{0.1}Ti_{0.9}O_{3-δ} catalyst with the overstretched A-site deficiency of 25% is remarkable.

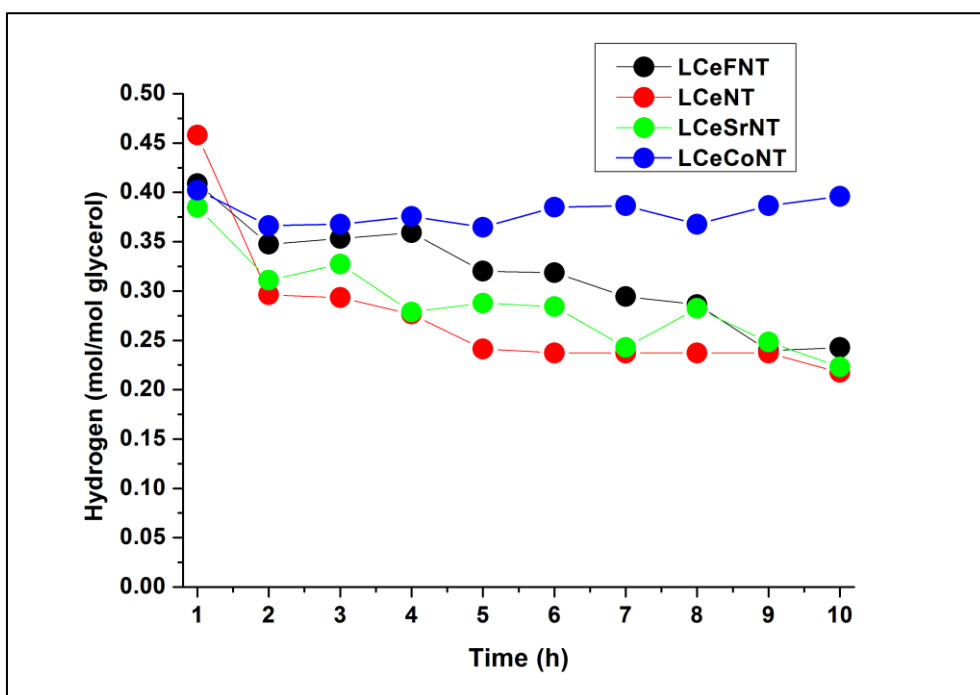


Figure 7 Comparing catalytic activity and stability of the catalysts by monitoring how hydrogen production (mol/mol of glycerol) changes over time for ten hours.

Generally, the catalytic activity and hydrogen production seems more stable with $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ and $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ catalyst systems over time. The sustained performance attest to the robust properties of the catalyst systems particularly their A-site deficiency and oxygen storage-release properties of ceria which are known to enhance oxygen ion mobility that facilitated the effective oxidation of carbonaceous decomposition products from glycerol pyrolysis and consequently hindered catalyst deactivation by coking activity or poisoning. This compares with work reported by Neagu et al, (2015) [23] and Papaioannou et al (2019) [24] and Macedo et al (2022) [37]. The relatively enhanced performance of $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ and $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ is also as results of the synergic contribution of the metal dopants in the alloy of Fe-Ni and Co-Ni active sites exsolved on the catalysts surface which tends to be more active than a single metal sites [24,57,58]. Hence, the disparity in their performance could be traced to not only extent of defect in them but also their difference in the chemical constituents [37-39]. Consequently, suffice it to say defect chemistry and constituent metals or dopants could play an important role in tailoring perovskite structures for better catalytic behaviour and should be explored in designing robust catalyst systems.

3.4 Control of carbon deposition activities

The resistant of the catalyst systems to carbon deposition on their surfaces during catalytic activity was investigated to further support their robust properties. Prolong usage of the catalyst exposes their surfaces to lots of carbonaceous residues of different structures and types from the biomass decomposition products that block active sites, pores and consequent deactivation of catalyst thereby limiting the life span and reusability of the catalyst [59-61]. The spent catalyst systems after ten hours of steam reforming of glycerol was subjected to temperature programmed oxidation in oxygen atmosphere and reaction condition stated in section 2.2. above. During temperature programmed oxidation, all the carbon deposited on the catalyst surface was converted to CO₂ by oxidation and characterised by identifying their type and location as well as level or extent of coking. The TGA profile in Figure 8 represents the extent or level of carbon deposition whilst the CO₂ peaks suggests the temperature at which bulk of the carbon oxidised to CO₂ which depends on the nature and location of the carbon on the catalyst surface.

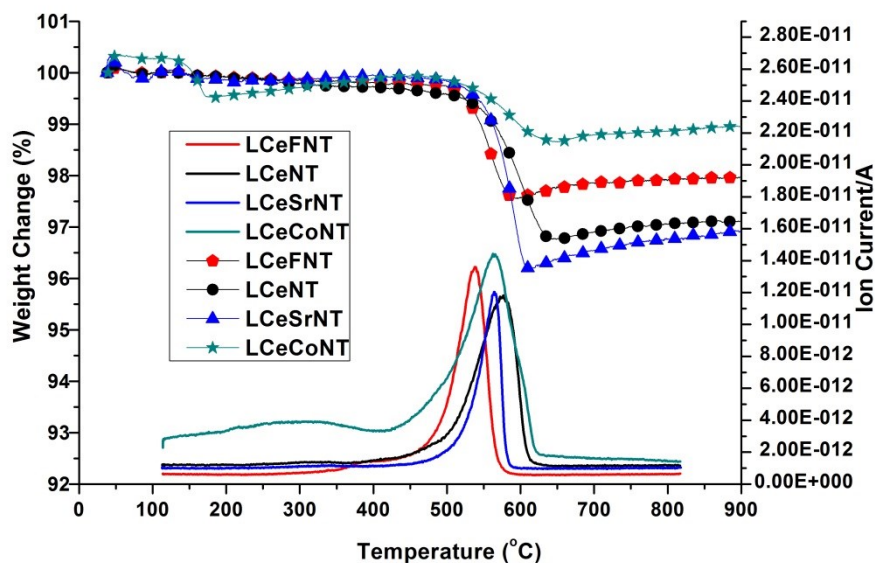


Figure 8 Oxidation of surface carbon and the corresponding change in weight of the used metal substituted A-site deficient titanate perovskite in oxidising atmosphere monitored in parallel with resultant CO₂ as a function of temperature. The temperature at which oxidation of surface carbon occurs is indicated by the CO₂ peak which depends on the nature and location of the carbon whilst the TGA profile shows the extent of coking.

Evidently, the gentle weight loss of the TGA profile suggests that all the catalyst have shown resistant and suppression of carbon deposition and suffered only a mild coking

activities which corroborates reported behaviour of catalyst systems prepared by exsolution [22,62,63]. Highest weight loss of 3.56% (0.72mg) and 2.80% (0.99 mg) was observed for $\text{La}_{0.6}\text{Ce}_{0.05}\text{Sr}_{0.1}\text{Ni}_{0.1}\text{Ti}_{0.9}\text{O}_{3-\delta}$ and $\text{La}_{0.8}\text{Ce}_{0.1}\text{Ni}_{0.4}\text{Ti}_{0.6}\text{O}_{3-\delta}$ respectively attributable to their high nickel populated surfaces resulting from their robust exsolution which attracted much surface C-C and C-O bond cleavages and formation of other products [37]. It is also interesting to observe that the catalysts systems $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ and $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ that formed alloy of Co-Ni and Fe-Co respectively have shown superior stability to coking activities than the mono-metal exsolved catalysts used in this work. This observation favourably compares with the findings reported in related work [24,58] as well as results reported on the use of modifiers [36-38]. The CO_2 peaks which indicates the temperature at which bulk of the carbon was oxidised depending upon the nature and location of the carbon on catalyst surface shows that oxidations occurred at 500-600 °C in all the catalysts. This suggests polymeric or graphitic carbon deposited at metal-support interphase though $\text{La}_{0.7}\text{Ce}_{0.1}\text{Co}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ and $\text{La}_{0.7}\text{Ce}_{0.1}\text{Fe}_{0.3}\text{Ni}_{0.1}\text{Ti}_{0.6}\text{O}_{3-\delta}$ are at lower temperature relatively which indicates traces of easy-to-oxidise amorphous carbon deposited on the catalyst metal surface as a results of their peculiar properties suggesting higher oxidative regeneration and reusability tendencies of the catalysts comparable to precious metal based catalysts [39].

Generally, all the catalysts have demonstrated good ability to suppress carbon deposition activities that could lead to deactivation. This is attributed to the lattice A-site deficiency and ceria's basic-acidic as well oxygen storage-release properties that enhanced oxygen mobility and other surface properties that facilitated the oxidation of carbonaceous decomposition products that could cause carbon deposition [36,37,39]. The titanates used as support has added extra stability and redox properties that enhanced oxidation of carbon residues from glycerol decomposition on the catalyst surfaces and suppression of coking activities which similarly compares with a related work [22] . Although the correlation between the coking activity and A-site deficiency or defect amongst the catalyst systems is not exhaustive from this work, however it compares with other related work that have shown defect due to A-site deficiency enhances oxygen mobility in the lattice which facilitates oxidation of the carbonaceous products and therefore limits carbon deposition [22].

4.0 Conclusion and Future Perspective

Some new catalyst systems were designed and developed and have demonstrated high activity, stability and suppression of catalyst deactivation by sintering and carbon deposition in steam reforming of glycerol. The results has shown that enhanced B-site metal catalyst exsolution, surface morphology and other catalyst surface properties such as catalyst-support interaction, particle size and distribution for effective catalytic behaviour could be achieved through tailoring of defect chemistry and choice of A-site metal dopant ions. The doping of Ceria in the A-site of the perovskite catalyst has significantly enhanced and mediated the B-site metal catalyst (Ni, Co and Fe and corresponding alloys) exsolution compared to none ceria containing A-site metal dopants such as Ca, Sr and Cr ions. The metal catalyst were anchored and socketed on the titanate support with improved catalyst-support interaction, particle size and distribution as well as thermal stability against sintering and agglomeration. The exsolution design and ceria dopant has also enhanced the reducibility of the nickel particles catalyst and robust structural properties compared to those prepared by wet impregnation. The exsolved nano metals (Fe, Ni and Co) forms alloys and the synergic contribution of the dopant metals in the exsolved alloyed nanoparticle catalyst yielded a better catalytic behaviour, stability and suppression of carbon deposition activities than the mono-metal exsolved catalysts nanoparticles. Overstretching of doping ratio by 0.5% has also yielded robust exsolution of the nano-catalyst, good catalytic behaviour and suppression of carbon deposition due to increased defect from A-deficiency with no apparent structural damage or instability. Consequently, defect chemistry due to A-site deficiency and careful selection of metal dopants could be used to design catalyst systems with enhanced robust surface properties and improved catalytic behaviour.

Acknowledgements

I thank the Petroleum Technology Development Fund, Nigeria for funding this research and University of St Andrews, Scotland UK for the opportunity to do my PhD programme with them.

REFERENCES

1. Asif M, Munir T, Energy supply its demand and security issues for developed and emerging economies. *Renew Sust Energ Revie* 2007, 11:1388–1413.
2. Shekhawat D, Spivey JJ, Berry DA, Fuel Cells: Technology for fuel Processing. Elsevier, 2011, 1-128.
3. Lo Faro M, Antonucci V, Antonucci PL, Aricò AS, Fuel flexibility: A key challenge for SOFC technology. *Fuel* 2012;102;554–559.
4. Bentley, R. W. Global oil and gas depletion: An overview. *Energy Policy* 2002; 30:189–205.
5. Casas Y, Arteaga LE, Morales M, Rosa E, Peralta, LM, Dewulf J, Energy and exergy analysis of an ethanol fueled solid oxide fuel cell power plant. *Chem Eng J* 2010;162:1057–1066
6. Nobrega SD, Galesco MV, Girona K, de Florio D Z, Steil MC, Georges S, Fonseca FC, Direct ethanol solid oxide fuel cell operating in gradual internal reforming. *J Power Sources* 2012; 213:156-159
7. Fan L, Tu Z, Chan SH, Recent development of hydrogen and fuel cell technologies: A review. *Energy Reports* 2021;7:8421-8446
8. Ahmed S, Krumpelt M, Hydrogen from hydrocarbon fuel for fuel cells. *Int j hydrog energy* 2001;26:291-301
9. Gross MD, Vohs JM, Gorte RJ, Recent progress in SOFC anodes for direct utilization of hydrocarbons. *J. Mater. Chem.* 17, 3071-3077 (2007)
10. Fan, X. Burton, R Zhou Y, Glycerol (by product of biodiesel production) as source for fuels and chemicals—mini review. *The Open Fuels & Energy Science Journal* 2010;3:17–22
11. Liu W, Liu C, Gogoi P, Deng, Y. Overview of Biomass Conversion to Electricity and Hydrogen and Recent Developments in Low-Temperature Electrochemical Approaches. *Engineering* 2020;6:1351-1363
12. Dauenhauer P J, Salge JR, Schmidt LD, Renewable hydrogen by autothermal steam reforming of volatile carbohydrates. *J Catal* 2006;244:238–247
13. Wu G, Zhang C, Li S, Han Z, Wang T, Ma X, Gong J Hydrogen production via glycerol steam reforming over Ni/Al₂O₃: Influence of nickel precursors. *ACS Sustain Chem. Eng.* 2013;1:1052–1062
14. Archer AS, Steinberger-Wilckens R, Systematic analysis of biomass derived fuels for fuel cells. *Int J Hydrog Energy* 2018;43;23178-23192

15. McIntosh, S. and Gorte, R. J. Direct hydrocarbon solid oxide fuel cells. *Chem. Rev.* 104, 4845-4865 (2004)
16. Adhikari S, Fernando S, Gwaltney SR, Filip To SD, Bricka RM, Steele PH, Haryanto AA, thermodynamic analysis of hydrogen production by steam reforming of glycerol. *Int J Hydrog Energy* 2007;32:2875 – 2880
17. Sanchez EA, Comelli RA, Hydrogen by glycerol steam reforming on a nickel–alumina catalyst: Deactivation processes and regeneration. *Int J Hydrog Energy* 2012;37:14740 – 14746
18. Sun W, Wei H, An LY, Jin C, Wu H, Xiong Z, Pu C, Sun C, Oxygen vacancy mediated $\text{La}_{1-x}\text{Ce}_x\text{FeO}_{3-\delta}$ perovskite oxides as efficient catalysts for CWAO of acrylic acid by A-site Ce doping. *Applied Catalysis B: Environmental* 2019;15:20-28
19. Yuan B, Tao Y, Qi S, Xie A, Luo S, Effect of A, B-site cation on the catalytic activity of $\text{La}_{1-x}\text{A}_x\text{Mn}_{1-y}\text{B}_y\text{O}_3$ (A =Ce, B = Ni) oxides for perovskite-type oxides for toluene oxidation. *Environ Sci Pollut Res.* 2022
20. Kwon O, Joo S, Choi S, Sengodan S, Kim G, Review on exsolution and its deriving forces. *J. Phys. Energy* 2020;2:032001
21. Kousi K, Tang C, Metcalfe IS, Neagu, D, Emergence and Future of Exsolved Materials. *Small* 2006479 2021, 1-27
22. Umar, A, Neagu D, John TS Irvine, Alkaline modified A-site deficient perovskite catalyst surface with exsolved nanoparticles and functionality in biomass valorisation. *Biofuel Res J* 2021; 29:1342-1350
23. Neagu D, Oh T, Miller DN, Menard H, Bukhari SM, Gamble SR, Gorte RJ, Vohs J.M., Irvine JTS, Nano-socketed nickel particles with enhanced coking resistance grown in situ by redox exsolution. *Nat. Commun.* 2015;6: 8120
24. Papaioannou EI, Neagu D, Ramli WKW, Irvine JTS, Metcalfe IS, Sulfur-tolerant exsolved Fe-Ni alloy nanoparticles for CO oxidation. *Topics in Catalysis* 2019; 62:1149-1156.
25. Valdye PD, Rodrigues A E, Glycerol for hydrogen production; A review. *Chem Eng Technol* 2009;32:1463 -1469
26. Adhikari S, Fernando SD, Haryanto A, Hydrogen production from glycerol: An update. *Energy Conversion and Management* 2009;50:2600-2604
27. Lo Faro M, Minutoli M, Monforte G, Antomui V, Arico A S, Glycerol oxidation in solid oxide fuel cells based on Ni – perovskite electro catalyst. *Biomass and Bioenergy* 2011; 35:1075-1084
28. Lin Y. Catalytic volarization of glycerol to hydrogen and syngas. *Int. j. hydrogen energy.* 38, 2678-2700 (2013)

29. Umar A, Irvine JTS, Gasification of glycerol over Ni/ γ -Al₂O₃ for hydrogen production: Tailoring catalytic properties to control deactivation. *Catal, Sustain. Energy* 2020;7:65-74
30. Boaro M, Colussi S, Trovarelli, A. Ceria-Based materials in hydrogenation and reforming reactions for CO₂ valorization. *Front Chem* 2019;7:28.
31. Gao N, Cheng M, Quan C, Zheng, Y, Syngas production via combined dry and steam reforming of methane over Ni-Ce/ZSM-5 catalyst. *Fuel* 2020;273:117702
32. Bezen MCI, Breitkopf C, Kolli NEI, Krafft J, Louis C, Lercher JA, Selective modification of the acid–base properties of ceria by supported Au. *Chem. Eur. J.* 2011;17 :7095 – 7104
33. Aneggi E, Boaro M, de Leitenburg C, Dolcetti G, Trovarelli A, Insights into the redox properties of ceria-based oxides and their implications in catalysis. *Journal of Alloys Compd* 2006;40:412 1096–1102
34. Bunluesin T, Gorte RJ, Graham GW, Studies of the water-gas-shift reaction on ceria-supported Pt, Pd, and Rh: Implications for oxygen-storage properties. *Appl Catal B: Environmental* 1998;15:107-114
35. Gorte RJ, Zhao S, Studies of the water-gas-shift reaction with ceria-supported precious metals. *Catalysis Today* 2005;104:18–24
36. Charisiou ND, Siakavelas G., Tzounis L, Dou B, Sebastian V, Hinder SJ, Baker MA, Polychronopoulou K, Goula MA, Ni/Y₂O₃-ZrO₂ catalyst for hydrogen production through the glycerol steam reforming reaction. *Int J Hydrog Energy* 2020;45:10442-10460
37. Macedo MS, Kraveva E, Ehrich H, Soria MA, Madeira LM, Hydrogen production from glycerol steam reforming over Co-based catalysts supported on La₂O₃, AlZnOx and AlLaOx. *Int J Hydrog Energy* 2022;47; 33239-33258
38. Charisiou ND, Siakavelas G, Papageridis KN, Baklavaridis A, Tzounis L, Polychronopoulou K, Goula MA, Hydrogen production via the glycerol steam reforming reaction over nickel supported on alumina and lanthana-alumina catalysts. *Int J Hydrog Energy* 2017;42:13039-13060.
39. Silva JM, Ribeiro LS, Órfão JJM, Soria MA, Madeira LM, Low temperature glycerol steam reforming over a Rh-based catalyst combined with oxidative regeneration. *Int J Hydrogen Energy* 2019; 44:2461-2473.
40. Nishihata Y, Mizuki J, Akao T, Tanaka H, Uenishi M, Kimura M, Okamoto T, Hamada N, Self-regeneration of a Pd-perovskite catalyst for automotive emissions control *Nature* 2002;418:164-167
41. Tanaka H, Uenishi M, Taniguchi M, Tan I, Narita K, Kimura M, Kaneko K, Nishihata Y, Mizuki J, The intelligent catalyst having the self-regenerative function of Pd, Rh and Pt for automotive emissions control. *Catal Today* 2006 ;117:321–328

42. Neagu D, Tsekouras G, Miller DN, Menard H, Irvine JTS, *In situ* growth of nanoparticles through control of non-stoichiometry. *Nature Chemistry* 2013;5:916-923
43. Neagu D, Oh T; Miller DN, Menard H, ; Bukhari SM, Gamble SR, Gorte RJ, Vohs JM, Irvine JTS, Nano-socketed nickel particles with enhanced coking resistance grown in situ by redox exsolution. *Nat. Commun.* 2015; 6:8120
44. Liu S, Chuang KT, Luo J-L. Double-layered perovskite anode with in situ exsolution of a Co-Fe alloy to cogenerate ethylene and electricity in a proton conduction ethane fuel cell. *ACS Catal* 2015; 6:760-768
45. Neagu D, Papaioannou EI, Ramli WKW, Miller DN, Murdoch BJ, Menard H, Umar, A, Barlow AJ, Cumpson PJ, Irvine JTS, Mettcalfe I, Demonstration of chemistry through restructuring and catalytic activation at anchored nanoparticles. *Nat Commun*, 2017;8:1855
46. Tsekouras G, Neagu D, Irvine JTS, Step-Change in high temperature steam electrolysis performance of perovskite oxide cathodes with exsolution of B-site dopants. *Energy Environ Sci* 2013;6:256-266
47. Trimm DL, Thermal Stability of Catalyst Support. *Studies in Surface Science and Catalysis* 1991;68:29-51
48. Andrievski R A, Review of thermal stability of nanomaterials. *J Mater Sci* 2014;49:1449-1460
49. Trovarelli A, Boaro M, Rocchini E, Leitenburg C, Dolcetti G, Some recent developments in the characterization of ceria-based catalysts *J Alloys Compd* 2001; 323:324 584–591
50. Evans CD, Kondrat SA, Smith PJ, Manning TD, Miedziak PJ, Brett GL, Armstrong RD, Bartley JK, Taylor SH, Rosseinsky MJ, Hutchings GJ, The preparation of large surface area lanthanum based perovskite supports for AuPt nanoparticles: tuning the glycerol oxidation reaction pathway by switching the perovskite B site. *Faraday Discussion* 2016;188:427-450
51. Yasutake T, Shinichi N, Isamu M, Shuichi K, Kengo S, Noboru Y, Synthesis of manganite perovskites by reverse homogeneous precipitation method in the presence of alkylammonium cation. *Chem Lett* 2000; 29:1202-1203
52. Lindenthal L, Rameshan R, Summerer H, Ruh T, Popovic J, Nenning A, Löffler S, Opitz AK, Blaha P, Rameshan C, Modifying surface structure of perovskite-based catalysts by nanoparticle exsolution. *Catalyst* 2020;10:2-14
53. Afzal S, Quan X, Zhang J, High surface area mesoporous nanocast LaMO₃ (M= Mn, Fe) perovskite for efficient catalytic ozonation and an insight into probable catalytic mechanism. *Appl Catal B: Environ* 2017;206:692-703

54. Chen C, Meng Z, Wang Z, Large specific surface area macroporous nano catalyst $\text{LaFe}_{1-x}\text{Ni}_x\text{O}$: A stable catalyst for catalytic methane dry reforming. *Hindawi J Chem* 2019;1-9
55. Merkulov R, Samigullin RR, Markov A, Patrakeev MV, Impact of A-site Cation deficiency on charge transport in $\text{La}_{0.5-x}\text{Sr}_{0.5}\text{FeO}_{3-d}$. *Materials* 2021;14
56. Nguyen TL, Dokiya M, Wang S, Tagawa H, Hashimoto T, The effect of oxygen vacancy on the oxide ion mobility in LaAlO_3 -based oxides. *Solid State Ionics* 2000;229-241
57. Tang C, Kousi K, Neagu D, Metcalfe IS, Trends and progress in bimetallic exsolution. *Chem Eur J* 2021
58. Tsiotsias AI, Charisiou, ND, Yentekakis IV, Goula MA. Bimetallic Ni-based catalysts for CO_2 Methanation: A Review. *Nanomaterials* 2021;11: 28
59. Cheng CK, Foo SY, Adesina AA, Carbon deposition on bimetallic $\text{Co-Ni/Al}_2\text{O}_3$ catalyst during steam reforming of glycerol. *Catal Today* 2011; 164: 268–274
60. Bartholomew CH, Mechanism of catalyst deactivation. *Applied Catalysis A: General* 2002;212:17-60
61. Rostrup-Nielsen J Mechanism of carbon formation on Ni-containing catalysts. *J. Catal.* 1977;48:155-165
62. Sun Y, Li J, Zhang Y, Hua B, Luo J, Bifunctional catalyst of core-shell nanoparticles socketed on oxygen-deficient layered perovskite for soot combustion: In situ observation of synergic dual active sites. *ACS Catal* 2016;6:2710-2714
63. Urasaki K, Sekine Y, Kawabe S, Kikuchi E, Matsukata M, Catalytic activities and coking resistance of Ni/perovskites in steam reforming of methane. *Applied Catalysis A: General* 2005;286:23-29