

Strategic Modulation of the Photonic Properties of Conjugated Organometallic Pt-Ir Polymers Exhibiting Hybrid CT Excited States

Ahmed M. Soliman, Eli Zysman-Colman*[†] and Pierre D. Harvey*


Contribution from the Département de chimie, Université de Sherbrooke, Sherbrooke, Québec, Canada J1K 2R1.

Correspondence: Pierre D. Harvey, email: Pierre.Harvey@USherbrooke.ca and Eli Zysman-Colman, email: eli.zysman-colman@st-andrews.ac.uk

[†]Current address: EaStCHEM School of Chemistry, Rm 254, Purdie Building, North Haugh University of St. Andrews, St Andrews, Fife, UK KY16 9ST. URL: www.zysman-colman.com

Contribution for the special issue on Metallo-polymers (guest editors: Schubert, Manners, and Newkome)

Abstract: Polymer **6**, ($[trans\text{-Pt}(\text{PBU}_3)_2(\text{C}\equiv\text{C})_2]\text{-}[\text{Ir}(\text{dFMeppy})_2(\text{N}^{\wedge}\text{N})](\text{PF}_6)_n$), ($[\text{Pt}]\text{-}[\text{Ir}](\text{PF}_6)_n$; $\text{N}^{\wedge}\text{N}$ = 5,5'-disubstituted-2,2'-bipyridyl; dFMeppy = 2-(2,4-difluorophenyl)-5-methylpyridine) has been prepared along with model compounds. These complexes were investigated by absorption and emission spectroscopy and their photophysical and electrochemical properties were measured and compared with their corresponding non-fluorinated complexes. Density functional theory (DFT) and time-dependent DFT computations corroborate the nature of the excited state as being a hybrid between the metal-to-ligand charge transfer ($^1,^3\text{MLCT}$) for the $trans\text{-Pt}(\text{PBU}_3)_2(\text{C}\equiv\text{C}\text{Ar})_2$ unit, $[\text{Pt}]$ and the metal-to-ligand/ligand-to-ligand' charge transfer ($^1,^3\text{ML}'\text{CT}/\text{LL}'\text{CT}$) for $[\text{Ir}]$ with L = dFMeppy . Overall, the fluorination of the phenylpyridine group expectedly does not change the nature of the excited state but desirably induces a small blue shift of the absorption and emission bands along a slight decrease in emission quantum yields and lifetimes.

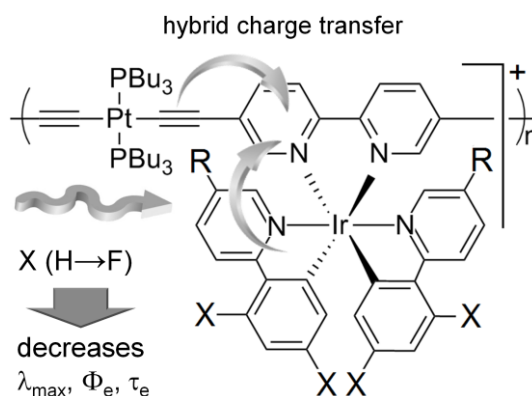

appropriate substitution. We now report the effect of fluorination of polymer **12**, providing polymer **6**. The combination of the anticipated strong blue shift of the absorption and emission bands due to fluorination, and the red-shift due to conjugation with [Pt] along the polymer backbone, leads to a small blue shift (only ~10 nm) of the spectral features, hence providing the desired effect.

Results and Discussion. The model complexes **1-5** and polymer **6** were synthesized in reasonable yields from dimer **13** [(dFMeppy)₂Ir-μ-Cl]₂ following procedures used for the corresponding non-fluorinated derivatives.^[4-7] Their syntheses and characterization are placed in the Experimental Section (SI). The absorption and emission spectra of **3-6** exhibit the characteristic signature expected for the [Ir] motif (Figure 2).^[4-8] The spectroscopic and photophysical data of **1-6** are compared to those for **7-12** in Table 1.

Table 1. Comparison of the spectral and photophysical data of **1-6** vs **7-12**.^{a,b}

	Abs. (nm) 298 K [ϵ ($\times 10^4$ M ⁻¹ cm ⁻¹)]	λ_{\max} (nm) 77 K	λ_{\max} (nm) 298 K	Φ_e (%)	τ_e (μ s) 77K	τ_e (μ s) 298K
1	250 [5.2]; 265 [5.2]; 315 [3.1]; 330 [2.4]; 365 [0.8]; 425 [0.1]	490	561	5.8	4.46	0.51
2	255 [3.8]; 265 [3.6]; 290 [3.0]; 315 [2.5]; 330 [2.5]; 345 [2.6]; 385 [0.4]; 450 [0.1]	523	575	2.5	4.40	0.13
3	255 [5.8]; 310 [3.2]; 395 [2.4]	556	614	11.4	14.3	4.57
4	250 [6.3]; 265 [4.2]; 310 [3.4], 350 [2.4], 400 [4.8]	544	567	11.6	10.4	2.51
5	255 [5.6]; 310 [3.3]; 350 [2.1]; 425 [3.8]; 450 [3.9]	593	632	1.9	6.11	1.93
6	250 [3.9]; 260 [3.2]; 315 [1.2], 415 [1.2], 485 [0.1]	547 592 640	628	1.0	4.81 4.22	0.8
7	265 [2.3]; 310 [1.0]; 325 [0.9]; 380 [0.2]; 450 [0.1]	536	623	8.5	4.12	0.16
8	250 [4.2]; 280 [3.3]; 315 [2.3]; 370 [0.8]	558	638	1.6	2.65	0.09
9	260 [3.7]; 315 [2.0]; 390 [1.9]	557	611	8.3	3.4	0.72
10	260 [6.8]; 300 [4.1]; 350 [4.0]; 370 [4.0], 460 [0.2]	547	595	31.9	11	2.9
11	255 [9.8]; 315 [5.1]; 415 [7.9]; 435 [9.1]	550 595 651	560 613 663	3.3	5.9	2.3
12	250 [0.3]; 280 [0.2]; 340 [0.1]; 435 [0.2]	558 596 654	555 617 655	2.6	5.7 3.3	2.5 1.9

a) The data for **7-12** are from references [4-6] and for **1** from reference [7]. b) The uncertainties on $\lambda_{\max} = \pm 2$ nm, on $\Phi_e = 10$ %, and on $\tau_e \approx 5$ %. For **6**, **11** and **12**, the τ_e 's were measured at one, two or three different wavelengths.

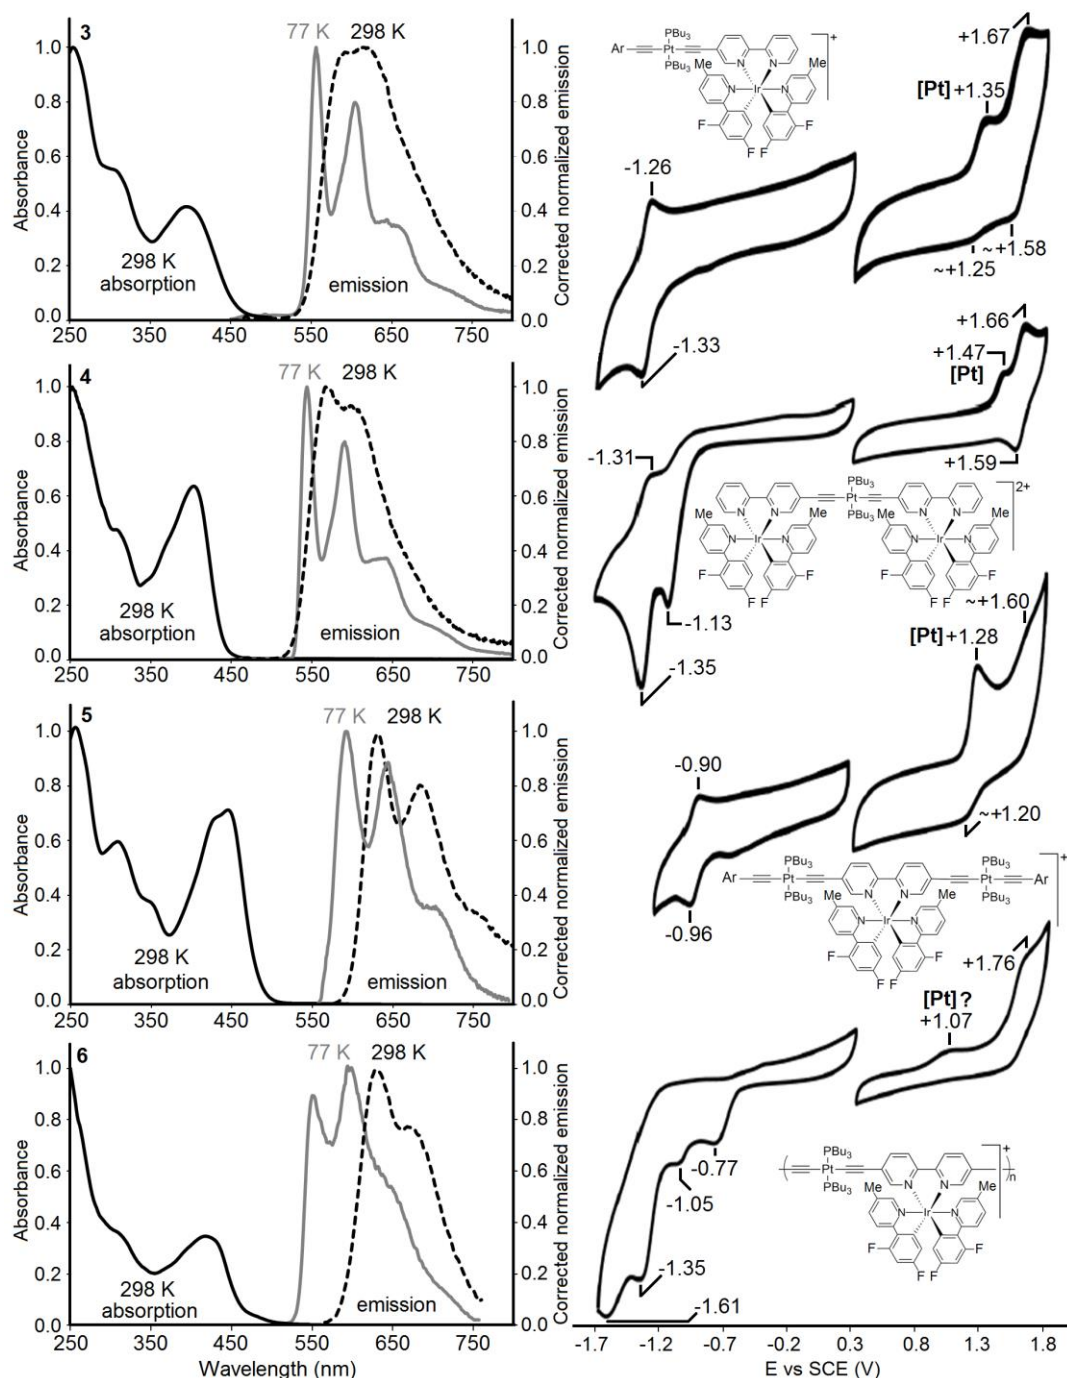


Figure 2. Left: absorption (black —) and emission (grey —, 77; black ---, 298 K) of **3-6** in 2MeTHF at 298 K. Right: cyclic voltammograms of **3-6** in degassed ACN at 298 K. Scan rate = 200 mV/s with 0.1 M *n*-Bu₄NPF₆ as the supporting electrolyte. **All waves are associated with [Ir] except those labelled [Pt] (i.e. *trans*-Pt(PBu₃)₂(aryl)₂).**

Spectroscopically, two main observations are striking (Table 1). First, a significant blue shift of the absorption and emission bands is noted upon fluorination of the complexes when comparing **1** vs **7** and **2** vs **8**. This behavior is fully consistent with the ML'CT/LL'CT nature of the excited states where the F-atom is withdrawing

electronic density on the ppy ligand. Second, this blue shift is smaller for the polymers (**6** vs **12**). This attenuation of F-inductive effect is explained by the hybrid nature of the excited state between the C≡C-linked **[Pt]** and **[Ir]** units that contributes to spread the electron withdrawing pull over a larger segment of the polymer. In a photophysical point of view, the Φ_e and τ_e data for **1-6** are similar or at least in the same order of magnitude as those for **7-12**. However, these parameters are globally smaller for the **1-6** compared to **7-12** (including polymer **6** vs **12**) indicating that the non-radiative rate constant, k_{nr} , is larger for the fluorinated species.

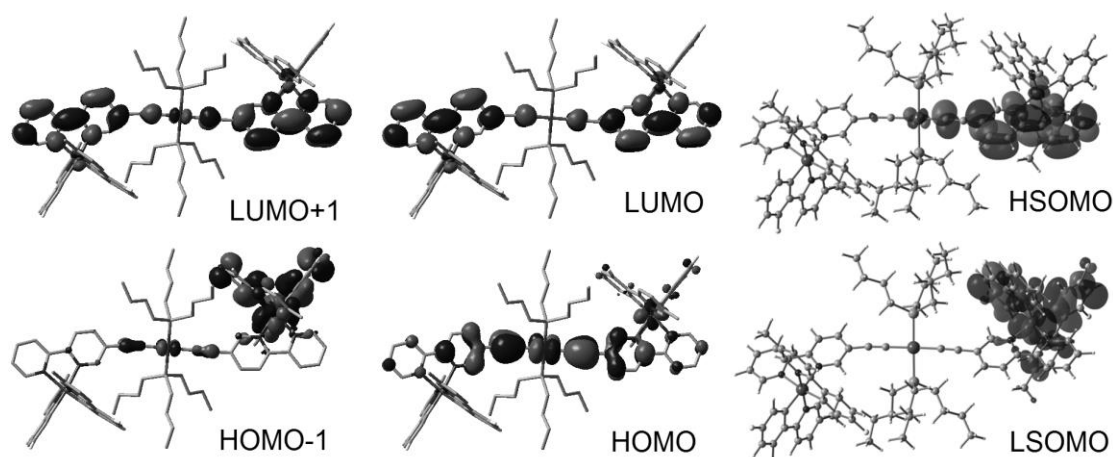


Figure 3. MO drawings of the frontier orbitals of the model **4** (left) and the HSOMO and LSOMO (right). The detail of the DFT and TDDFT calculations are in the SI.

The nature of the S_1/T_1 excited states was corroborated by DFT calculations (Figure 3). Indeed for model **4**, the HOMO is composed of the π -system centered on the **[Pt]** unit with minor atomic contributions of the bipyridine fragments (bpy). The HOMO-1 and -2 are composed of atomic components of the dFMeppy π -systems with a minor contribution of the central **[Pt]** unit. The LUMO and LUMO+1 exhibit contributions from the N[^]N π^* -systems, with a minor atomic component located on **[Pt]**. The TDDFT computations for **4** predict that the two lowest energy singlet-singlet electronic transitions are placed at 465.8 ($f = 0.0188$) and 463.5 nm ($f = 0.003$) with weak oscillator strengths (f). The positions of these 0-0 peaks corroborate well with the experimental spectrum where a weak tail extends all the way to 465 nm (Figure 2). These two transitions are respectively composed of HOMO-1 \rightarrow LUMO (45%), HOMO-1 \rightarrow LUMO+1 (35%), HOMO \rightarrow LUMO (12%) and HOMO-2 \rightarrow LUMO (67%), HOMO-2 \rightarrow LUMO+1 (31%), hence confirming the hybrid nature of the singlet excited states discussed above. The calculated difference in total energy between the S_0 and T_1 states

is 2.377 eV, which places the triplet state at 522 nm. This value compares favorably to the one observed at 77 K (i.e. 544 for **4** and 547 nm for **6**). The computed highest and lowest semi-occupied MO's (respectively HSOMO and LSOMO) exhibit atomic contributions mostly located in the N[^]N and dFMepy π -systems, respectively, inferring that the nature of the excited state is (ML'CT/LL'CT) of the [Ir] chromophore. Overall, these computations indicate that presented substitution pattern expectedly does not affect the nature of the S₁ and T₁ states for this type of chromophore, i.e. ([Ir]-[Pt]⁺)_n.

The cyclic voltammograms, CV, of **3-6** are presented in Figure 2 and the peak positions are placed in Table 2 (when both cathodic and anodic waves are observable, only the averaged peak positions are reported in this table for simplicity). **The assignment for each waves indicated in the figure caption is based on previous CV analysis for 1 (and its dimer) and *trans*-C₆H₅C≡C-PtL₂-C≡CC₆H₅ and its derivatives (L = phosphine).**^[7,9] The fact that E_{1/2red}(**1**) < E_{1/2red}(**7**) and E_{1/2ox}(**1**) > E_{1/2ox}(**7**) is consistent with the expected withdrawing effect of the fluorine atoms. When one electron rich [Pt] unit is conjugated to the [Ir] one, this effect is almost completely cancelled (E_{1/2red}(**3**) ~ E_{1/2red}(**9**) and E_{1/2ox}(**3**) ~ E_{1/2ox}(**9**)), which is exactly the effect sought. However, the peak positions are dependent upon the relative number of [Pt] and [Ir] units for the short oligomers. Indeed, E_{1/2red}(**4**) < E_{1/2red}(**10**) and E_{1/2ox}(**4**) > E_{1/2ox}(**10**) (one [Pt] for two [Ir]) again witnessing the withdrawing effect for the fluorine, and E_{1/2red}(**5**) > E_{1/2red}(**11**) and E_{1/2ox}(**5**) < E_{1/2ox}(**11**) (two [Pt] for one [Ir]), which is consistent with the donating ability of the conjugated rich [Pt] unit. Based on these models, one readily suspects that for polymers wherein the number of [Pt] and [Ir] units being about the same, an approximate cancellation of the withdrawing and donating effects should be observed. This is in fact not the case. In comparison with the short oligomers, both polymers turned out to be both easier to oxidize and to reduce (i.e. lower positive and negative potentials). This property is fully consistent with the presence of an extended conjugation. However, the drawback is that all waves are either electrochemically irreversible or chemically irreversible making this sought analysis unreliable. Indeed, the data do not explain why polymer **6** is both harder to oxidize and to reduce than polymer **12**, and why the potential difference between |E_{1/2ox}| and |E_{1/2red}|, ΔE , is significantly smaller for **12** than for **6** and all the model complexes.

Table 2. Electrochemical data for **1**, **3-6**, **7**, **9-12**

	$E_{1/2ox}$	ΔE	$E_{1/2red}$		$E_{1/2ox}$	ΔE	$E_{1/2red}$
1	1.58 ^a	2.71	-1.13 ^a	7	1.27 ^a	2.48	-1.21 ^a
3	1.30 ^c 1.63 ^b	2.60	-1.30 ^a	9	1.34 ^a 1.60 ^a	2.68	-1.34 ^a
4	1.47 ^c 1.63 ^b	2.60	-1.13 ^c -1.33 ^c	10	1.31 ^a	2.67	-1.36 ^a
5	1.24 ^c ~ 1.70 ^c	2.17	-0.93 ^a	11	1.36 ^c	2.71	-1.35 ^c
6	1.07 ^c 1.76 ^c	1.84	-0.77 ^c -1.05 ^c -1.35 ^c -1.61 ^c	12	0.71 ^c 1.22 ^c 1.34 ^c	1.11 - - -	-0.40 ^c -0.77 ^c -0.93 ^b -1.29 ^b

All in V vs SCE, the data for **1** are from reference [7] and for **7**, **9-12** are from reference [6]; a = e.r. (electrochemically reversible), b = c.r. (chemically reversible), c = ir (irreversible), $\Delta E = |E_{1/2ox}| + |E_{1/2red}|$.

Conclusion. The hybrid nature of the conjugated (**[Ir]-[Pt]**)_n polymers in their excited state contributes to modulate their desired electronic properties *via* simple inductive effects. Indeed, from an electronic and spectroscopic standpoint, the withdrawing pull of the fluorine atoms on the C^N ligands of **[Ir]** compensates for the red-shifting effect of the conjugated **[Pt]** unit within the chain on the absorption and emission bands of the polymers was successful, i.e. within ~10 nm. Including the electron donating push of the **[Pt]** unit, these three individual effects (electron withdrawing and donating effects, along with conjugation) could be readily observed by cyclic voltammetry measurements using the model compounds in comparison with the polymers. This strategy, which is particularly convenient, simple and predictable, appears as a reliable approach for the future design of conjugated **[Ir]**-containing polymers.

Experimental Section: see Supporting Information (SI).

Acknowledgements. This research was supported by the Natural Sciences and Engineering Research Council of Canada (NSERC).

References

- [1] a) K. P. S. Zanoni, B. K. Kariyazaki, A. Ito, M. K. Brennaman, T. J. Meyer, I. Murakami, Y. Neyde, *Inorg. Chem.*, **2014**, *53*, 4089; b) G. E. Schneider, A. Pertegas, E.

C. Constable, C. E. Housecroft, N. Hostettler, C. D. Morris, J. A. Zampese, J. A., H. J. Bolink, J. M. Junquera-Hernandez, E. Orti, M. Sessolo, *J. Mat. Chem. C: Mat. Opt. Elec. Devices*, **2014**, 2, 7047; c) R. Srivastava, L. R. Joshi, *Phys. Chem. Chem. Phys.* **2014**, 16, 17284; d) P. Li, G-G. Shan, H-T. Cao, D-X. Zhu, Z-M. Su, R. Jitchati, M. R. Bryce, *Eur. J. Inorg. Chem.*, **2014**, 2014, 2376; e) N. Darmawan, C-H. Yang, M. Mauro, R. Froehlich, L. De Cola, C-H. Chang, Z-J. Wu, C-W. Tai, *J. Mat. Chem. C: Mat. Opt. Elec. Devices*, **2014**, 2, 2569; f) H. Tang, L. Wei, J. Wang, Y. Li, H. Wu, W. Yang, Y. Cao, *Syn. Met.*, **2014**, 187, 209; g) T. Akatsuka, C. Roldan-Carmona, E. Orti, H. J. Bolink, *Adv. Mat.*, **2014**, 26, 770; h) K. Hasan, L. Donato, Y. Shen, J. D. Slinker, E. Zysman-Colman, *Dalton Trans.*, **2014**, 43, 13672; i) E. C. Constable, C. D. Ertl, C. E. Housecroft, J. A. Zampese, *Dalton Trans.*, **2014**, 43, 5343; j) G. E. Schneider, H. J. Bolink, E. C. Constable, C. D. Ertl, C. E. Housecroft, A. Pertegas, J. A. Zampese, A. Kanitz, F. Kessler, S. B. Meier, *Dalton Trans.*, **2014**, 43, 1961; k) E. C. Constable, C. E. Housecroft, P. Kopecky, C. J. Martin, I. A. Wright, J. A. Zampese, H. J. Bolink, A. Pertegas, *Dalton Trans.*, **2014**, 42, 8086; l) S. Evariste, M. Sandroni, T. W. Rees, C. Roldán-Carmona, L. Gil-Escrig, H. J. Bolink, E. Baranoff, E. Zysman-Colman *J. Mater. Chem. C*, **2014**, 2, 5793.

[2] a) H. J. Park, J. N. Kim, H-J. Yoo, K-R. Wee, S. O. Kang, D. W. Cho, U. C. Yoon, *J. Org. Chem.*, **2013**, 78, 12281; b) L. J. Rono, H. G. Yayla, D. Y. Wang, M. F. Armstrong, R. R. Knowles, *J. Am. Chem. Soc.*, **2013**, 135, 17735; c) F. Dumur, M. Lepeltier, B. Graff, E. Contal, G. Wantz, J. Lalevee, C. R. Mayer, D. Bertin, D. Gigmes, *Syn. Met*, **2013**, 182, 13; d) K. Mori, Y. Kubota, H. Yamashita, *Chem. Asian J.*, **2013**, 8, 3207; e) S. Lee, S-O. Kim, H. Shin, H-J. Yun, K. Yang, S-K. Kwon, J-J. Kim, Y-H. Kim, *J. Am. Chem. Soc.*, **2013**, 135, 14321; f) D. Tordera, J. J. Serrano-Perez, A. Pertegas, E. Orti, H. J. Bolink, E. Baranoff, Md. K. Nazeeruddin, J. Frey, *Chem. Mater.*, **2013**, 25, 3391; g) H. J. Park, J. N. Kim, H-J. Yoo, K-R. Wee, S. O. Kang, D. W. Cho, U. C. Yoon, *J. Org. Chem.*, **2013**, 78, 8054; h) H-H. Chou, Y-K. Li, Y-H. Chen, C-C. Chang, C-Y. Liao, C-H. Cheng, *ACS Appl. Mater. Interfaces*, **2013**, 5, 6168; i) Y. Shen, D. D. Kuddes, C. A. Naquin, T. W. Hesterberg, C. Kusmierz, B. J. Holliday, J. D. Slinker, *Appl. Phys. Lett.* **2013**, 102, 203305/1; j) T. Hu, L. Duan, J. Qiao, L. He, D. Zhang, L. Wang, Y. Qiu, *Syn. Met*, **2013**, 163, 33; k) Y. Zhou, S. Han, G. Zhou, W-Y Wong, V. A. L. Roy, *Appl. Phys. Lett.*, **2013**, 102, 083301; l) N. M. Shavaleev, R. Scopelliti, M. Grätzel, M. K. Nazeeruddin, A. Pertegas, C.

Roldan-Carmona, D. Tordera, H. J. Bolink, *J. Mat. Chem. C: Mat. Opt. Elec. Devices*, **2013**, *1*, 2241; m) M. Sessolo, D. Tordera, Daniel; H. J. Bolink, *ACS Appl. Mater. Interfaces*, **2013**, *5*, 630; n) S. van Reenen, T. Akatsuka, D. Tordera, Daniel, M. Kemerink, H. J. Bolink, *J. Am. Chem. Soc.*, **2013**, *135*, 886; o) S. B. Meier, S. van Reenen, B. Lefevre, D. Hartmann, H. J. Bolink, A. Winnacker, W. Sarfert, M. Kemerink, *Adv. Funct. Mater.*, **2013**, *23*, 3531; p) J. M. Fernández-Hernández, S. Ladouceur, Y. Shen, A. Iordache, X. Wang, L. Donato, S. Gallagher-Duval, M. de Anda Villa, J. D. Slinker, L. De Cola, E. Zysman-Colman *J. Mater. Chem. C*, **2013**, *1*, 7440; q) C.-L.; Ho, W.-Y. Wong, *Coord. Chem. Rev.* **2013**, *257*, 1614; r) Y. Zhou, S. Han, G. Zhou, W.-Y. Wong, V. A. L. Roy *Appl. Phys. Lett.* **2013**, *102*, 083301/1.

[3] a) T. Guo, L. Yu, B. Zhao, Y. Li, Y. Tao, W. Yang, Q. Hou, H. Wu, Y. Cao, *Macromol. Chem. Phys.*, **2012**, *213*, 820; b) T. Guo, R. Guan, J. Zou, J. Liu, L. Ying, W. Yang, H. Wu, Y. Cao, *Polym. Chem.*, **2011**, *2*, 2193; c) F. Dumur, Y. Guillaneuf, A. Guerlin, G. Wantz, D. Bertin, F. Miomandre, G. Clavier, D. Gigmes, C. R. Mayer, *Macromol. Chem. Phys.* **2011**, *212*, 1616; d) J. W. Levell, J. P. Gunning, P. L. Burn, J. Robertson, I. D. W. Samuel, *Org. Electron*, **2010**, *11*, 1561; e) T. W. Hesterberg, X. Yang, B. Holliday, *J. Polyhedron*, **2010**, *29*, 110; f) B. Liang, Y. Xu, Z. Chen, J. Peng, Y. Cao, *Synthetic Metals*, **2009**, *159*, 1876; g) B. Liang, L. Wang, Y. Xu, H. Shi, Y. Cao, *Adv. Funct. Mater.*, **2007**, *17*, 3580; h) H. Zhen, J. Luo, W. Yang, Q. Chen, L. Ying, J. Zou, H. Wu, Y. Cao, *J. Mater. Chem.*, **2007**, *17*, 2824; i) S.-J. Liu, Q. Zhao, Y. Deng, Y.-J. Xia, J. Lin, Q.-L. Fan, L.-H. Wang, W. Huang, *J. Phys. Chem. C*. **2007**, *111*, 1166.

[4] A. M. Soliman, D. Fortin, E. Zysman-Colman, P. D. Harvey, *Macromol. Rapid Commun.*, **2012**, *33*, 522.

[5] A. M. Soliman, D. Fortin, P. D. Harvey, E. Zysman-Colman, *Chem. Commun.*, **2012**, *48*, 1120.

[6] A. M. Soliman, D. Fortin, E. Zysman-Colman, P. D. Harvey, *Chem. Commun.*, **2012**, *48*, 6271.

[7] A. M. Soliman, D. Fortin, P. D. Harvey, E. Zysman-Colman, *Dalton Trans.*, **2012**, *41*, 9382.

[8] G. Zhou, Y. He, B. Yao, J. Dang, W.-Y. Wong; Z. Xie, X. Zhao, L. Wang, *Chem. Asian J.* **2010**, *5*, 2405.

[9] T. Kenny, S. Lamare, S. M. Aly, D. Fortin, G. Brisard, P. D. Harvey *Inorg. Chem.* **2012**, *51*, 13081.